



King's Research Portal

[Link to publication record in King's Research Portal](#)

Citation for published version (APA):

T2K Collaboration, Collaboration, T. TK., Abe, K., Akhlaq, N., Akutsu, R., Ali, A., Alt, C., Andreopoulos, C., Barker, G. J., Blondel, A., Carter, A. J., Cartwright, S. L., Coleman, J., Cook, L., Lodovico, F. D., Doyle, T. A., Finch, A. J., Harris, D. A., Jenkins, S. J., ... Zsoldos, S. (2022). *Scintillator ageing of the T2K near detectors from 2010 to 2021*.

Citing this paper

Please note that where the full-text provided on King's Research Portal is the Author Accepted Manuscript or Post-Print version this may differ from the final Published version. If citing, it is advised that you check and use the publisher's definitive version for pagination, volume/issue, and date of publication details. And where the final published version is provided on the Research Portal, if citing you are again advised to check the publisher's website for any subsequent corrections.

General rights

Copyright and moral rights for the publications made accessible in the Research Portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognize and abide by the legal requirements associated with these rights.

- Users may download and print one copy of any publication from the Research Portal for the purpose of private study or research.
- You may not further distribute the material or use it for any profit-making activity or commercial gain
- You may freely distribute the URL identifying the publication in the Research Portal

Take down policy

If you believe that this document breaches copyright please contact librarypure@kcl.ac.uk providing details, and we will remove access to the work immediately and investigate your claim.

Scintillator ageing of the T2K near detectors from 2010 to 2021



The T2K Collaboration

K. Abe,⁶⁰ N. Akhlaq,⁴⁹ R. Akutsu,⁶⁶ A. Ali,^{71,66} C. Alt,¹⁰ C. Andreopoulos,^{58,37} M. Antonova,¹⁹ S. Aoki,³² T. Arihara,⁶³ Y. Asada,⁷³ Y. Ashida,³³ E.T. Atkin,²¹ S. Ban,³³ M. Barbi,⁵⁰ G.J. Barker,⁷⁰ G. Barr,⁴⁶ D. Barrow,⁴⁶ M. Batkiewicz-Kwasniak,¹⁴ F. Bench,³⁷ V. Berardi,²² L. Berns,⁶⁹ S. Bhadra,⁷⁴ A. Blanchet,⁵⁷ A. Blondel,^{57,12} S. Bolognesi,⁵ T. Bonus,⁷² S. Bordoni,¹² S.B. Boyd,⁷⁰ A. Bravar,¹² C. Bronner,⁶⁰ S. Bron,¹² A. Bubak,⁵⁶ M. Buizza Avanzini,³⁶ N.F. Calabria,²³ S. Cao,²⁰ A.J. Carter,⁵² S.L. Cartwright,⁵⁵ M.G. Catanesi,²² A. Cervera,¹⁹ J. Chakrani,³⁶ D. Cherdack,¹⁶ G. Christodoulou,¹¹ M. Cicerchia,^{24,*} J. Coleman,³⁷ G. Collazuol,²⁴ L. Cook,^{46,29} A. Cudd,⁶ Yu.I. Davydov,³⁹ A. De Roeck,¹¹ G. De Rosa,²³ T. Dealtry,³⁴ C.C. Delogu,²⁴ C. Densham,⁵⁸ A. Dergacheva,²⁶ F. Di Lodovico,³¹ S. Dolan,¹¹ D. Douqa,¹² T.A. Doyle,³⁴ O. Drapier,³⁶ K.E. Duffy,⁴⁶ J. Dumarchez,⁵⁷ P. Dunne,²¹ K. Dygнарowicz,⁶⁸ A. Eguchi,⁵⁹ S. Emery-Schrenk,⁵ A. Ershova,⁵ S. Fedotov,²⁶ P. Fernandez,³⁷ A.J. Finch,³⁴ G.A. Fiorentini Aguirre,⁷⁴ G. Fiorillo,²³ M. Friend,^{15,†} Y. Fujii,^{15,†} Y. Fukuda,⁴¹ K. Fusshoeller,¹⁰ C. Giganti,⁵⁷ V. Glagolev,³⁹ M. Gonin,²⁸ E.A.G. Goodman,¹³ A. Gorin,²⁶ M. Grassi,²⁴ M. Guigue,⁵⁷ D.R. Hadley,⁷⁰ J.T. Haigh,⁷⁰ P. Hamacher-Baumann,⁵³ D.A. Harris,⁷⁴ M. Hartz,^{66,29} T. Hasegawa,^{15,†} S. Hassani,⁵ N.C. Hastings,¹⁵ A. Hatzikoutelis,^{34,‡} Y. Hayato,^{60,29} A. Hiramoto,³³ M. Hogan,⁷ J. Holeczek,⁵⁶ A. Holin,⁵⁸ T.J. Holvey,⁴⁶ N.T. Hong Van,^{20,27} T. Honjo,⁴⁵ F. Jacob,²⁴ A.K. Ichikawa,⁶⁹ M. Ikeda,⁶⁰ T. Ishida,^{15,†} M. Ishitsuka,⁶⁴ H.T. Israel,⁵⁵ S.J. Ives,²¹ K. Iwamoto,⁵⁹ A. Izmaylov,²⁶ N. Izumi,⁶⁴ M. Jakkapu,¹⁵ B. Jamieson,⁷¹ S.J. Jenkins,⁵⁵ C. Jesús-Valls,¹⁷ J.J. Jiang,⁴³ P. Jonsson,²¹ C.K. Jung,^{43,§} P.B. Jurj,²¹ M. Kabirnezhad,⁷⁴ A.C. Kaboth,^{52,58} T. Kajita,^{61,§} H. Kakuno,⁶³ J. Kameda,⁶⁰ S.P. Kasetti,³⁸ Y. Kataoka,⁶⁰ Y. Katayama,⁷³ T. Katori,³¹ M. Kawaue,³³ E. Kearns,^{3,29,§} M. Khabibullin,²⁶ A. Khotjantsev,²⁶ T. Kikawa,³³ H. Kikutani,⁵⁹ S. King,³¹ J. Kisiel,⁵⁶ A. Knight,⁷⁰ T. Kobata,⁴⁵ T. Kobayashi,^{15,†} L. Koch,¹⁸ G. Kogan,²¹ A. Konaka,⁶⁶ L.L. Kormos,³⁴ Y. Koshio,^{44,§} A. Kostin,²⁶ K. Kowalik,⁴² Y. Kudenko,^{26,¶} S. Kuribayashi,³³ R. Kurjata,⁶⁸ T. Kutter,³⁸ M. Kuze,⁶²

*also at INFN-Laboratori Nazionali di Legnaro

†also at J-PARC, Tokai, Japan

‡now at San José State University, San José, California, U.S.A.

§affiliated member at Kavli IPMU (WPI), the University of Tokyo, Japan

¶also at Moscow Institute of Physics and Technology (MIPT), Moscow region, Russia and National Research Nuclear University "MEPhI", Moscow, Russia

M. La Commara,²³ **L. Labarga,**¹ **J. Lagoda,**⁴² **S.M. Lakshmi,**⁴² **M. Lamers James,**^{34,58}
I. Lamont,³⁴ **M. Lamoureux,**²⁴ **D. Last,**⁴⁷ **N. Latham,**⁷⁰ **M. Laveder,**²⁴ **M. Lawe,**³⁴ **Y. Lee,**³³
C. Lin,²¹ **T. Lindner,**⁶⁶ **S.-K. Lin,**³⁸ **R.P. Litchfield,**¹³ **S.L. Liu,**⁴³ **A. Longhin,**²⁴ **K.R. Long,**^{21,58}
L. Ludovici,²⁵ **X. Lu,**⁷⁰ **T. Lux,**¹⁷ **L.N. Machado,**²³ **L. Magaletti,**²² **K. Mahn,**⁴⁰ **M. Malek,**⁵⁵
M. Mandal,⁴² **S. Manly,**⁵¹ **A.D. Marino,**⁶ **L. Marti-Magro,**⁷³ **D.G.R. Martin,**²¹ **M. Martini,**^{57,||}
J.F. Martin,⁶⁵ **T. Maruyama,**^{15,†} **T. Matsubara,**¹⁵ **V. Matveev,**²⁶ **C. Mauger,**⁴⁷ **K. Mavrokoridis,**³⁷
E. Mazzucato,⁵ **N. McCauley,**³⁷ **J. McElwee,**⁵⁵ **K.S. McFarland,**⁵¹ **C. McGrew,**⁴³ **A. Mefodiev,**²⁶
G.D. Megias,^{54,61} **L. Mellet,**⁵⁷ **C. Metelko,**³⁷ **M. Mezzetto,**²⁴ **A. Minamino,**⁷³ **O. Mineev,**²⁶
S. Mine,⁴ **M. Miura,**^{60,§} **L. Molina Bueno,**¹⁹ **S. Moriyama,**^{60,§} **Th.A. Mueller,**³⁶ **D. Munford,**¹⁶
L. Munteanu,⁵ **K. Nagai,**⁷³ **Y. Nagai,**⁹ **T. Nakadaira,**^{15,†} **K. Nakagiri,**⁵⁹ **M. Nakahata,**^{60,29}
Y. Nakajima,⁵⁹ **A. Nakamura,**⁴⁴ **H. Nakamura,**⁶⁴ **K. Nakamura,**^{29,15,†} **Y. Nakano,**⁶⁰
S. Nakayama,^{60,29} **T. Nakaya,**^{33,29} **K. Nakayoshi,**^{15,†} **C.E.R. Naseby,**²¹ **T.V. Ngoc,**^{20,#}
V.Q. Nguyen,⁵⁷ **K. Niewczas,**⁷² **Y. Nishimura,**³⁰ **K. Nishizaki,**⁴⁵ **F. Nova,**⁵⁸ **P. Novella,**¹⁹
J.C. Nugent,¹³ **H.M. O’Keeffe,**³⁴ **L. O’Sullivan,**⁵⁵ **T. Odagawa,**³³ **T. Ogawa,**¹⁵ **R. Okada,**⁴⁴
K. Okumura,^{61,29} **T. Okusawa,**⁴⁵ **R.A. Owen,**⁴⁹ **Y. Oyama,**^{15,†} **V. Palladino,**²³ **V. Paolone,**⁴⁸
M. Pari,²⁴ **J. Parlone,**³⁷ **S. Parsa,**¹² **J. Pasternak,**²¹ **M. Pavin,**⁶⁶ **D. Payne,**³⁷ **G.C. Penn,**³⁷
J.D. Perkin,⁵⁵ **D. Pershey,**⁸ **L. Pickering,**⁵² **C. Pidcott,**⁵⁵ **G. Pintaudi,**⁷³ **C. Pistillo,**²
B. Popov,^{57,**} **K. Porwit,**⁵⁶ **M. Posiadala-Zezula,**⁶⁷ **Y.S. Prabhu,**⁴² **B. Quilain,**³⁶
T. Radermacher,⁵³ **E. Radicioni,**²² **B. Radics,**¹⁰ **P.N. Ratoff,**³⁴ **M. Reh,**⁶ **C. Riccio,**⁴³ **E. Rondio,**⁴²
S. Roth,⁵³ **A. Rubbia,**¹⁰ **A.C. Ruggeri,**²³ **C.A. Ruggles,**¹³ **A. Rychter,**⁶⁸ **K. Sakashita,**^{15,†}
F. Sánchez,¹² **G. Santucci,**⁷⁴ **C.M. Schloesser,**¹⁰ **K. Scholberg,**^{8,§} **M. Scott,**²¹ **Y. Seiya,**^{45,††}
T. Sekiguchi,^{15,†} **H. Sekiya,**^{60,29,§} **D. Sgalaberna,**¹⁰ **A. Shaikhiev,**²⁶ **A. Shaykina,**²⁶
M. Shiozawa,^{60,29} **W. Shorrock,**²¹ **A. Shvartsman,**²⁶ **K. Skwarczynski,**⁴² **M. Smy,**⁴
J.T. Sobczyk,⁷² **H. Sobel,**^{4,29} **F.J.P. Soler,**¹³ **Y. Sonoda,**⁶⁰ **R. Spina,**²² **H. Su,**⁴⁸ **I.A. Suslov,**³⁹
S. Suvorov,^{26,57} **A. Suzuki,**³² **S.Y. Suzuki,**^{15,†} **Y. Suzuki,**²⁹ **A.A. Sztuc,**²¹ **M. Tada,**^{15,†}
S. Takayasu,⁴⁵ **A. Takeda,**⁶⁰ **Y. Takeuchi,**^{32,29} **H.K. Tanaka,**^{60,§} **Y. Tanihara,**⁷³ **M. Tani,**³³
V.V. Tereshchenko,³⁹ **N. Teshima,**⁴⁵ **N. Thamm,**⁵³ **L.F. Thompson,**⁵⁵ **W. Toki,**⁷ **C. Touramanis,**³⁷
T. Towstego,⁶⁵ **K.M. Tsui,**³⁷ **T. Tsukamoto,**^{15,†} **M. Tzanov,**³⁸ **Y. Uchida,**²¹ **A. Vacheret,**²¹
M. Vagins,^{29,4} **Z. Vallari,**^{43,§§} **D. Vargas,**¹⁷ **G. Vasseur,**⁵ **C. Vilela,**¹¹ **W.G.S. Vinning,**⁷⁰
T. Vladislavljevic,⁵⁸ **T. Wachala,**¹⁴ **A.V. Waldron,**^{46,¶¶} **J.G. Walsh,**³⁴ **Y. Wang,**⁴³ **L. Wan,**³
D. Wark,^{58,46} **M.O. Wascko,**²¹ **A. Weber,**¹⁸ **R. Wendell,**^{33,§} **M.J. Wilking,**⁴³ **C. Wilkinson,**³⁵
J.R. Wilson,³¹ **K. Wood,**³⁵ **C. Wret,**⁵¹ **J. Xia,**⁶¹ **Y.-h. Xu,**³⁴ **K. Yamamoto,**^{45,††} **C. Yanagisawa,**^{43,|||}
G. Yang,⁴³ **T. Yano,**⁶⁰ **K. Yasutome,**³³ **N. Yershov,**²⁶ **U. Yevarouskaya,**⁵⁷ **M. Yokoyama,**^{59,§}
Y. Yoshimoto,⁵⁹ **M. Yu,**⁷⁴ **R. Zaki,**⁷⁴ **A. Zalewska,**¹⁴ **J. Zalipska,**⁴² **K. Zaremba,**⁶⁸ **G. Zarnecki,**⁴²
X. Zhao,¹⁰ **T. Zhu,**²¹ **M. Ziembicki,**⁶⁸ **E.D. Zimmerman,**⁶ **M. Zito,**⁵⁷ **S. Zsoldos,**³¹

¹ *University Autonoma Madrid, Department of Theoretical Physics, 28049 Madrid, Spain*

|| also at IPSA-DRII, France

also at the Graduate University of Science and Technology, Vietnam Academy of Science and Technology

** also at JINR, Dubna, Russia

†† also at Nambu Yoichiro Institute of Theoretical and Experimental Physics (NITEP)

§§ now at California Institute of Technology, Pasadena, California, U.S.A.

¶¶ now at Imperial College London, London, United Kingdom

||| also at BMCC/CUNY, Science Department, New York, New York, U.S.A.

- ²*University of Bern, Albert Einstein Center for Fundamental Physics, Laboratory for High Energy Physics (LHEP), Bern, Switzerland*
- ³*Boston University, Department of Physics, Boston, Massachusetts, U.S.A.*
- ⁴*University of California, Irvine, Department of Physics and Astronomy, Irvine, California, U.S.A.*
- ⁵*IRFU, CEA, Université Paris-Saclay, F-91191 Gif-sur-Yvette, France*
- ⁶*University of Colorado at Boulder, Department of Physics, Boulder, Colorado, U.S.A.*
- ⁷*Colorado State University, Department of Physics, Fort Collins, Colorado, U.S.A.*
- ⁸*Duke University, Department of Physics, Durham, North Carolina, U.S.A.*
- ⁹*Eötvös Loránd University, Department of Atomic Physics, Budapest, Hungary*
- ¹⁰*ETH Zurich, Institute for Particle Physics and Astrophysics, Zurich, Switzerland*
- ¹¹*CERN European Organization for Nuclear Research, CH-1211 Genève 23, Switzerland*
- ¹²*University of Geneva, Section de Physique, DPNC, Geneva, Switzerland*
- ¹³*University of Glasgow, School of Physics and Astronomy, Glasgow, United Kingdom*
- ¹⁴*H. Niewodniczanski Institute of Nuclear Physics PAN, Cracow, Poland*
- ¹⁵*High Energy Accelerator Research Organization (KEK), Tsukuba, Ibaraki, Japan*
- ¹⁶*University of Houston, Department of Physics, Houston, Texas, U.S.A.*
- ¹⁷*Institut de Física d'Altes Energies (IFAE) - The Barcelona Institute of Science and Technology, Campus UAB, Bellaterra (Barcelona) Spain*
- ¹⁸*Institut für Physik, Johannes Gutenberg-Universität Mainz, Staudingerweg 7, 55128 Mainz, Germany*
- ¹⁹*IFIC (CSIC & University of Valencia), Valencia, Spain*
- ²⁰*Institute For Interdisciplinary Research in Science and Education (IFIRSE), ICISE, Quy Nhon, Vietnam*
- ²¹*Imperial College London, Department of Physics, London, United Kingdom*
- ²²*INFN Sezione di Bari and Università e Politecnico di Bari, Dipartimento Interuniversitario di Fisica, Bari, Italy*
- ²³*INFN Sezione di Napoli and Università di Napoli, Dipartimento di Fisica, Napoli, Italy*
- ²⁴*INFN Sezione di Padova and Università di Padova, Dipartimento di Fisica, Padova, Italy*
- ²⁵*INFN Sezione di Roma and Università di Roma "La Sapienza", Roma, Italy*
- ²⁶*Institute for Nuclear Research of the Russian Academy of Sciences, Moscow, Russia*
- ²⁷*International Centre of Physics, Institute of Physics (IOP), Vietnam Academy of Science and Technology (VAST), 10 Dao Tan, Ba Dinh, Hanoi, Vietnam*
- ²⁸*International Laboratory for Astrophysics, Neutrino and Cosmology Experiments, Kashiwanoha, Japan*
- ²⁹*Kavli Institute for the Physics and Mathematics of the Universe (WPI), The University of Tokyo Institutes for Advanced Study, University of Tokyo, Kashiwa, Chiba, Japan*
- ³⁰*Keio University, Department of Physics, Kanagawa, Japan*
- ³¹*King's College London, Department of Physics, Strand, London WC2R 2LS, United Kingdom*
- ³²*Kobe University, Kobe, Japan*
- ³³*Kyoto University, Department of Physics, Kyoto, Japan*
- ³⁴*Lancaster University, Physics Department, Lancaster, United Kingdom*
- ³⁵*Lawrence Berkeley National Laboratory, Berkeley, CA 94720, USA*
- ³⁶*Ecole Polytechnique, IN2P3-CNRS, Laboratoire Leprince-Ringuet, Palaiseau, France*
- ³⁷*University of Liverpool, Department of Physics, Liverpool, United Kingdom*
- ³⁸*Louisiana State University, Department of Physics and Astronomy, Baton Rouge, Louisiana, U.S.A.*
- ³⁹*Joint Institute for Nuclear Research, Dubna, Moscow Region, Russia*
- ⁴⁰*Michigan State University, Department of Physics and Astronomy, East Lansing, Michigan, U.S.A.*

- ⁴¹*Miyagi University of Education, Department of Physics, Sendai, Japan*
- ⁴²*National Centre for Nuclear Research, Warsaw, Poland*
- ⁴³*State University of New York at Stony Brook, Department of Physics and Astronomy, Stony Brook, New York, U.S.A.*
- ⁴⁴*Okayama University, Department of Physics, Okayama, Japan*
- ⁴⁵*Osaka City University, Department of Physics, Osaka, Japan*
- ⁴⁶*Oxford University, Department of Physics, Oxford, United Kingdom*
- ⁴⁷*University of Pennsylvania, Department of Physics and Astronomy, Philadelphia, PA, 19104, USA.*
- ⁴⁸*University of Pittsburgh, Department of Physics and Astronomy, Pittsburgh, Pennsylvania, U.S.A.*
- ⁴⁹*Queen Mary University of London, School of Physics and Astronomy, London, United Kingdom*
- ⁵⁰*University of Regina, Department of Physics, Regina, Saskatchewan, Canada*
- ⁵¹*University of Rochester, Department of Physics and Astronomy, Rochester, New York, U.S.A.*
- ⁵²*Royal Holloway University of London, Department of Physics, Egham, Surrey, United Kingdom*
- ⁵³*RWTH Aachen University, III. Physikalisches Institut, Aachen, Germany*
- ⁵⁴*Departamento de Física Atómica, Molecular y Nuclear, Universidad de Sevilla, 41080 Sevilla, Spain*
- ⁵⁵*University of Sheffield, Department of Physics and Astronomy, Sheffield, United Kingdom*
- ⁵⁶*University of Silesia, Institute of Physics, Katowice, Poland*
- ⁵⁷*Sorbonne Université, Université Paris Diderot, CNRS/IN2P3, Laboratoire de Physique Nucléaire et de Hautes Energies (LPNHE), Paris, France*
- ⁵⁸*STFC, Rutherford Appleton Laboratory, Harwell Oxford, and Daresbury Laboratory, Warrington, United Kingdom*
- ⁵⁹*University of Tokyo, Department of Physics, Tokyo, Japan*
- ⁶⁰*University of Tokyo, Institute for Cosmic Ray Research, Kamioka Observatory, Kamioka, Japan*
- ⁶¹*University of Tokyo, Institute for Cosmic Ray Research, Research Center for Cosmic Neutrinos, Kashiwa, Japan*
- ⁶²*Tokyo Institute of Technology, Department of Physics, Tokyo, Japan*
- ⁶³*Tokyo Metropolitan University, Department of Physics, Tokyo, Japan*
- ⁶⁴*Tokyo University of Science, Faculty of Science and Technology, Department of Physics, Noda, Chiba, Japan*
- ⁶⁵*University of Toronto, Department of Physics, Toronto, Ontario, Canada*
- ⁶⁶*TRIUMF, Vancouver, British Columbia, Canada*
- ⁶⁷*University of Warsaw, Faculty of Physics, Warsaw, Poland*
- ⁶⁸*Warsaw University of Technology, Institute of Radioelectronics and Multimedia Technology, Warsaw, Poland*
- ⁶⁹*Tohoku University, Faculty of Science, Department of Physics, Miyagi, Japan*
- ⁷⁰*University of Warwick, Department of Physics, Coventry, United Kingdom*
- ⁷¹*University of Winnipeg, Department of Physics, Winnipeg, Manitoba, Canada*
- ⁷²*Wroclaw University, Faculty of Physics and Astronomy, Wroclaw, Poland*
- ⁷³*Yokohama National University, Department of Physics, Yokohama, Japan*
- ⁷⁴*York University, Department of Physics and Astronomy, Toronto, Ontario, Canada*

ABSTRACT: The T2K experiment widely uses plastic scintillator as a target for neutrino interactions and an active medium for the measurement of charged particles produced in neutrino interactions at its near detector complex. Over 10 years of operation the measured light yield recorded by the scintillator based subsystems has been observed to degrade by 0.9–2.2% per year. Extrapolation of the degradation rate through to 2040 indicates the recorded light yield should remain above the lower threshold used by the current reconstruction algorithms for all subsystems. This will allow the near detectors to continue contributing to important physics measurements during the T2K-II and Hyper-Kamiokande eras. Additionally, work to disentangle the degradation of the plastic scintillator and wavelength shifting fibres shows that the reduction in light yield can be attributed to the ageing of the plastic scintillator.

KEYWORDS: Performance of High Energy Physics Detectors; Scintillators, scintillation and light emission processes (solid, gas and liquid scintillators); Neutrino detectors; Gamma detectors (scintillators, CZT, HPGe, HgI etc)

Contents

1	Introduction	2
1.1	The T2K Experiment	2
1.2	Scintillator Ageing	2
2	The T2K Scintillator Detectors	3
2.1	ND280	3
2.1.1	PØD	4
2.1.2	FGD	5
2.1.3	ECal	7
2.1.4	SMRD	7
2.2	INGRID	8
3	Light Yield Measurements	9
3.1	Data Samples	10
3.2	ND280	10
3.2.1	PØD	11
3.2.2	FGD	12
3.2.3	ECal	12
3.2.4	SMRD	12
3.3	INGRID	13
3.4	Light Yield Stability Uncertainty	14
3.4.1	ND280	14
3.4.2	INGRID	15
4	Annual Light Yield Reduction	15
5	Projected Future Response	18
6	Separation of ECal Scintillator and Fibre Degradation	19
6.1	Scintillator Degradation	21
6.2	Fibre Degradation	23
7	Conclusions	25

1 Introduction

1.1 The T2K Experiment

T2K (Tokai-to-Kamioka) is a long-baseline neutrino oscillation experiment [1] located in Japan, measuring muon (anti-)neutrino disappearance and electron (anti-)neutrino appearance from a muon (anti-)neutrino beam produced by the J-PARC (Japan Proton Accelerator Research Complex) synchrotron [2]. The experiment consists of a far detector at a distance of 295 km from J-PARC, a near detector complex 280 m downstream of the proton beam target, and the beam facility itself. The far detector is Super-Kamiokande [3], a 50 kt water Cherenkov detector positioned 2.5° off the beam axis.

The near detector complex contains ND280 [4] and INGRID [5] detectors which started operation in 2010. In addition, WAGASCI-BabyMIND [6, 7] was installed in 2019. INGRID is located directly on the beam axis, while ND280 is situated at the same off-axis angle as Super-Kamiokande. ND280 measures the rate of neutrino interactions before oscillation has occurred. This provides information on the neutrino flux, cross section and neutrino type which is necessary to predict the interaction rate at the far detector. INGRID monitors the neutrino beam direction and profile as well as the neutrino interaction event rate with high statistics.

Most subsystems of ND280, along with the INGRID detector, use plastic scintillator bars as an active detector medium. Whilst traversing the detector, charged particles excite electrons within the scintillator material to higher orbitals. The de-excitation of the electrons produces the emission of scintillation light which is used to track the passage of these particles. The scintillation light is collected by 1 mm diameter Kuraray wavelength-shifting (WLS) fibres [8] for transmission to Hamamatsu Multi-Pixel Photon Counters (MPPC) [9], a type of Silicon Photon Multiplier (SiPM) located at one or both ends of the scintillator bars.

T2K was the first experiment to employ MPPCs on a large scale, utilising $\sim 65,000$ MPPCs across the near detectors. The observed MPPC failure rate has been very low, at around $\sim 0.5\%$ of the total over the current lifetime of the experiment, and so their failure is not currently a concern for the future operation of the T2K near detectors.

However, during 10 years of operation some degradation in the light yield produced by the scintillator bars has occurred. Similar degradation has also been observed in other experiments, such as MINOS [10] and MINER ν A [11]. Understanding this effect is important for the accurate calibration of the detectors, for monitoring their long-term efficiency and predicting the future performance.

1.2 Scintillator Ageing

The issue of plastic scintillator ageing is long known [12], and there are many studies aimed at measuring, characterizing and developing stabilisation methods for these widely used materials (see for example [13–19]). These studies often consider the impact of potentially controllable environmental factors such as temperature and humidity on the long-term performance of the materials, as well as ways to chemically stabilise them.

The exact mechanism for scintillator ageing occurring within the T2K near detectors is unknown, but there are a number of potentially contributing factors:

- Mechanical stressing of the scintillator causing the development of crazes or shears within the material [20]. These inhibit the uniform scattering of light within the scintillator, preventing transmission through total internal reflection.
- Fogging of the scintillators due to water penetrating into the material and condensing [21]. This increases the opacity of the scintillator and is a significant problem where the materials are exposed to very high humidity conditions with large temperature variations.
- Oxidation of the scintillator through photochemical processes that lead to the production of peroxides causing the yellowing of the material [22]. This reduces the light yield from the scintillator and has been observed in the accelerated ageing test performed on the scintillator bars used by the MINOS experiment [10], which are materially identical to the INGRID, FGD, ECal and PØD subsystems of T2K as described in section 2.1.

Within this paper the relevant T2K near detector subsystems are described in section 2 and the data samples and light yield measurement methods used are detailed in section 3. The rate of degradation of the T2K scintillator is presented in section 4, along with predictions for the future response of the detectors in section 5 and an attempt to disentangle whether the ageing is dominated by the degradation of the scintillator or wavelength shifting (WLS) fibres in section 6.

2 The T2K Scintillator Detectors

2.1 ND280

The ND280 detector, figure 1, is composed of a set of subsystems enclosed within the refurbished UA1 magnet [23]. The subsystems are as follows:

- A detector composed of scintillator, water and brass target planes designed to identify π^0 s (PØD) [24].
- The tracker region, consisting of three time projection chambers (TPCs) [25] and two plastic scintillator fine-grained detectors (FGDs) [26], optimised to study charged current interactions of incoming neutrinos. The upstream FGD1 is entirely composed of scintillator planes, the downstream FGD2 consists of alternating modules of scintillator and water-filled volumes.
- Plastic scintillator and lead sampling electromagnetic calorimeters (ECals) that surround the PØD and tracker region [27].
- Plastic scintillator side muon range detectors (SMRDs) [28] situated in the magnet flux return yokes.

The coordinate system has z along the neutrino beam direction, and x and y are horizontal and vertical, respectively.

The material used in the PØD, FGD and ECal scintillator bars is polystyrene Dow Styron 663 W, doped with 1% PPO (2,5-diphenyloxazole) and 0.03% POPOP (1,4-bis(5-phenyloxazol-2-yl) benzene) and co-extruded with a surface layer of polystyrene loaded with 15% TiO₂ to allow diffuse reflection of scintillation light. The bars for the PØD and ECal were manufactured in

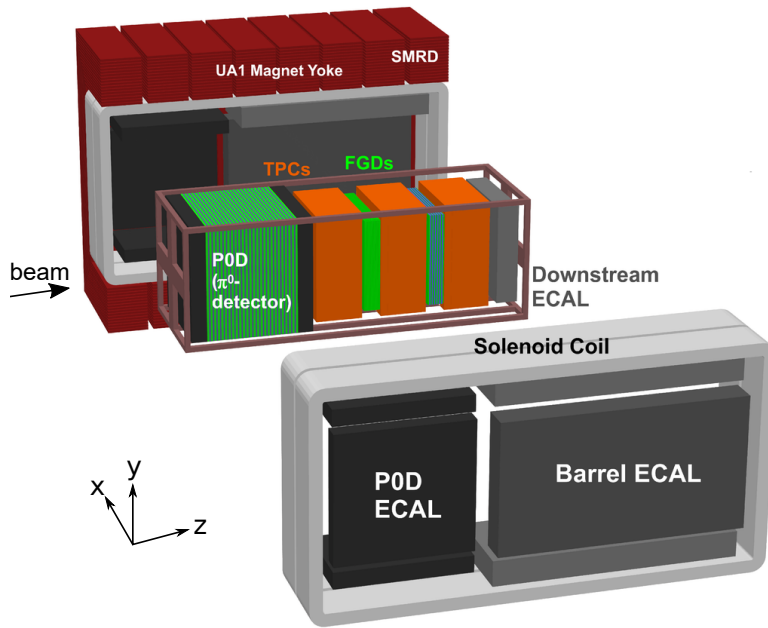


Figure 1: Exploded diagram of the ND280 off-axis near detector displaying the different detector subsystems.

Table 1: Scintillator production dates for each detector.

Detector	Production Period
PØD	2007–2008
ECal	2007–2009
FGD	2006
SMRD	2007–2008
INGRID	2007–2008

the extrusion facility at Fermi National Accelerator Laboratory (FNAL) and their composition is identical to that of the scintillator bars used in the MINOS experiment [10]. For the FGD, scintillator bars of the same composition were produced by extrusion procedure at Celco Plastics Ltd, Surrey, British Columbia. The scintillator bars of the SMRD use polystyrene doped with 1.5% PTP (1,4-Diphenylbenzene) and 0.01% POPOP and were chemically etched to produce a reflective coating. These were manufactured by the Uniplast company in Vladimir, Russia. All the ND280 scintillator bars were produced between 2006 and 2009 as shown in table 1.

All subsystems use Kuraray Y-11 blue to green WLS fibres for photon transmission to the MPPCs. The specific WLS formulations used are Y-11(175) S-35 J-type (PØD), Y-11(200) S-35 J-type (FGD), Y-11(200) CS-35 J-type (ECal) and Y-11(150) S-70 S-type (SMRD).

The particular geometry of each subsystem is described below.

2.1.1 PØD

The PØD detector consists of 40 scintillator modules called PØDules, as shown in figure 2. Each PØDule consists of two orthogonally oriented bar layers sandwiched between an inactive target and

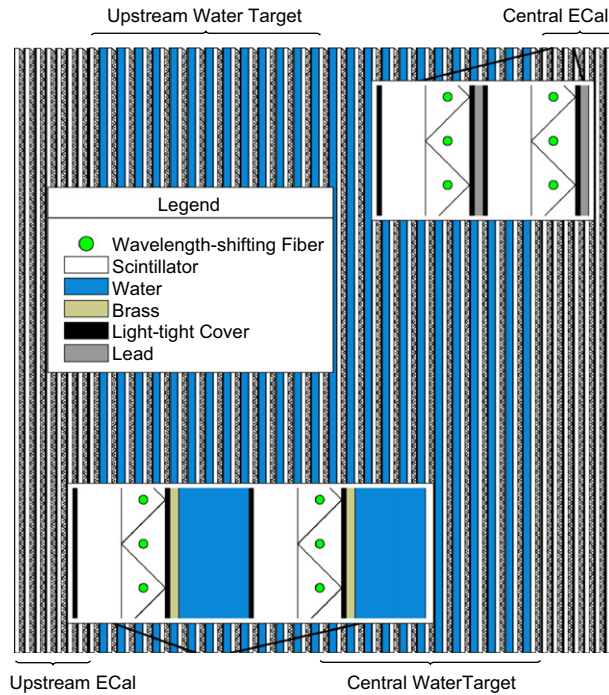


Figure 2: A schematic of the four PØD Super-PØDules as installed in the detector. The neutrino beam enters from the left hand side of the figure.


radiator material. The PØDules are perpendicular to the beam direction and are assembled into four constituent units called Super-PØDules, these are defined in the following way:

1. Super-PØDule 0: PØDules 0 - 6, the Upstream ECal.
2. Super-PØDule 1: PØDules 7 - 19, the Upstream Water Target.
3. Super-PØDule 2: PØDules 20 - 32, the Central Water Target.
4. Super-PØDule 3: PØDules 33 - 39, the Central ECal.


The scintillator bars in the PØD are triangular in cross section with a height of 17 mm and a width of 33 mm. Each bar has a single 2.6 mm diameter coaxial hole through which a WLS fibre is inserted, as shown in figure 3a. The horizontal bars are 2133 mm long and the vertical bars are 2272 mm long. The fibres are not secured within the bar, leaving an air gap between the bar and WLS fibre. The WLS fibres are mirrored with a vacuum deposition of aluminium on one end and are optically coupled to an MPPC on the other. A ferrule is glued to the end of the fibre which couples to a housing holding the MPPC, see figure 3b. A 3 mm thick polyethylene disk behind the MPPC provides pressure between the fibre and MPPC epoxy window. This design of fibre to MPPC coupling is also used by the ECal (see section 2.1.3).

2.1.2 FGD

The FGD scintillator bars are perpendicular to the beam in either the horizontal (X) or vertical (Y) direction, and are arranged into "XY" modules. Each module consists of a layer of 192 bars

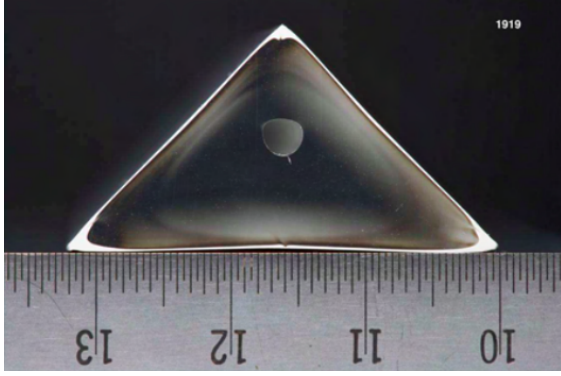


(a) End view of a PØD scintillator bar.

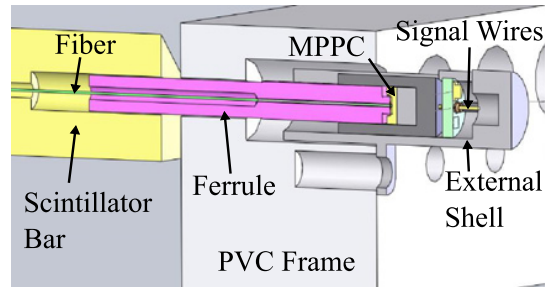


(b) A close-up view of the edge of a PØDule showing how the WLS fibers exit the scintillator bars and couple to the MPPCs.

Figure 3: PØD bar image (a) and MPPC connection schematic (b).

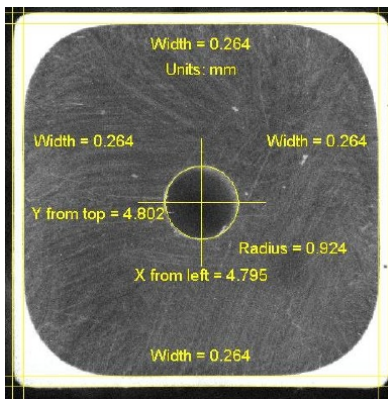


(a) Photo taken with a CCD camera of a typical FGD scintillator bar.

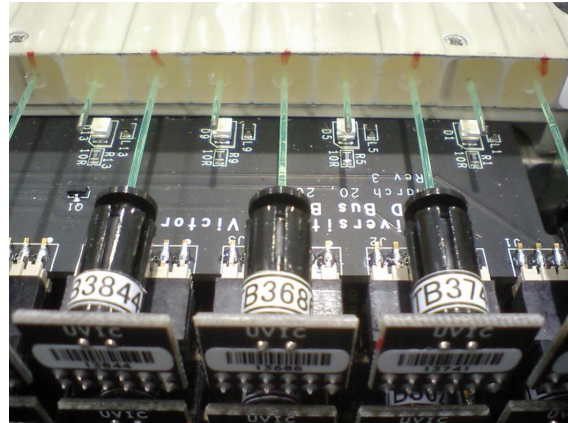


(b) Partial view of the end of a FGD scintillator layer with alternating fibres connected to MPPCs.

Figure 4: An image of a FGD scintillator bar (a) and a FGD scintillator layer (b).

in the horizontal direction glued to 192 bars in the vertical direction. The scintillator bars have a square cross section with a side width of 9.6 mm. The length of the bars is 1864 mm and each has a 1.8 mm diameter hole through its centre containing the WLS fibre, see figure 4a. One end of the fibre is mirrored with a vacuum deposition of aluminium to improve light collection efficiency, the other end is connected to an MPPC. The upstream FGD1 contains fifteen such modules while the downstream FGD2 contains seven modules interspersed with inactive water target layers. Each FGD module has dimensions of $1864 \times 1864 \times 20.2 \text{ mm}^3$ (not including electronics). There is an air gap between the scintillator and the fibre. The fibre extends only a few centimetres from one end of the bar to reach an MPPC as shown in figure 4b. The fibre is connected to the MPPC with a custom two part connector, one part glued to the fibre and the other holding the MPPC, latched together by mechanical force. Bicron BC600 glue was chosen to fix the coupler to the fiber. Within each layer, alternate bars are read out from alternating ends.

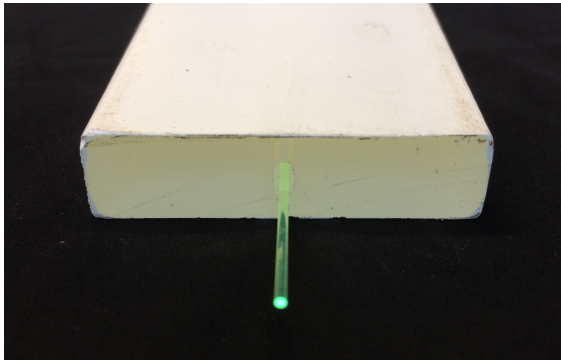

(a) End view of an ECal scintillator bar and WLS fibre.

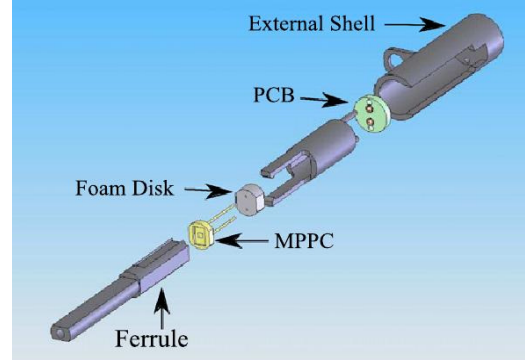

(b) Exploded diagram of WLS fibre to MPPC connector.


Figure 5: ECal scintillator bar with WLS fibre (a) and diagram of the WLS fibre to MPPC connector assembly (b).

2.1.3 ECal

The ECal scintillator bars have a cross section of $40 \times 10 \text{ mm}^2$ with a 2 mm diameter hole down the centre through which a WLS fibre passes, see figure 5a. There is an air gap between the scintillator and the fibre. The ECal is comprised of thirteen modules each of which uses one or two different lengths of scintillator bar in their construction. The Downstream (DS) ECal module has 1700 bars of length 2000 mm oriented in alternating vertical and horizontal layers perpendicular to the beam direction. Across the six Barrel ECal modules there are 3990 bars of length 3840 mm (Z bars) lying parallel to the beam direction. The four top and bottom barrel modules contain 6144 bars of length 1520 mm (X bars), and the two side barrel modules contain 3072 bars of length 2280 mm (Y bars). The Barrel X and Y bars are oriented perpendicular to the beam direction and have fibres which are mirrored on one end with a vacuum deposition of aluminium, while the other end is connected to an MPPC as shown in figure 5b. The Barrel Z and Downstream ECal bars have fibres which are connected to MPPCs on both ends. As will be described in section 3, the analysis methods used within this paper require the 3D reconstruction of muon tracks. As a result the six PØD ECal modules (not described) are not used in the studies presented as all the scintillator bars run parallel to the beam direction making the 3D reconstruction of particle tracks, needed for ageing studies, challenging. It should be noted that the Downstream ECal was installed into ND280 in early-2010, while the Barrel ECal modules were installed in late-2010.

2.1.4 SMRD

There are two types of SMRD scintillator bars with different sizes, horizontal ($7 \times 167 \times 875 \text{ mm}^3$) and vertical ($7 \times 175 \times 875 \text{ mm}^3$), grouped in modules of 4 and 5 respectively, see figure 6a. There are 404 modules in total with 768 (1240) horizontal (vertical) bars. The modules are placed in layers in the air gaps of the magnetic flux return yokes. The magnet yokes are numbered 1-8 going downstream along the beam direction. All yokes host three horizontal layers and yokes 1 through 5 also host three vertical layers. The most downstream yokes host more vertical layers: yoke 6 hosts four, and yokes 7 and 8 host six. Figure 6a shows the placement of the first layer of modules in a

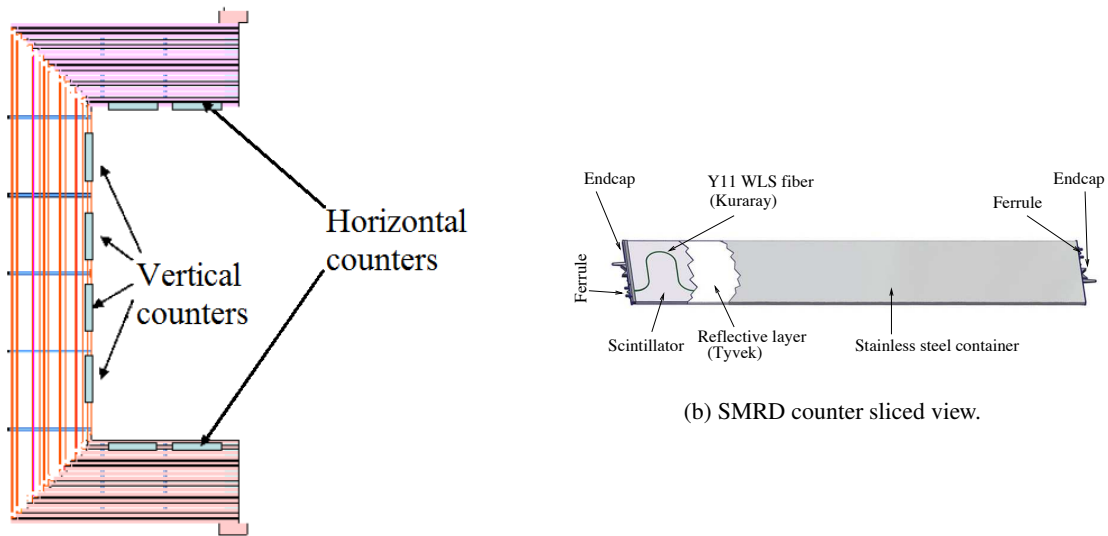

(a) Schematic view of a layer of SMRD modules.

Figure 6: Schematic view of SMRD module positions (a) and image of an SMRD counter design (b).

yoke segment. For better collection of the scintillator light and to improve the positional accuracy in the SMRD, S-shaped (curvature of $\varnothing = 58$ mm) WLS fibres run down the length of the bars as shown in figure 6b. The fibres are bent and glued into grooves within the scintillator bars using BC600 Bicon glue. It is worth noting that any degradation of this glue with time could have an impact on the light yield measured by the SMRD. The design results in nearly uniform response across the surface while reducing the number of channels to read out. The signal is read out from both ends of the bar via MPPCs. Each fibre exits through a ferrule which is part of a custom made endcap, glued and screwed to the scintillator, to which a connector with the MPPC is attached. A foam spring ensures a reliable coupling between the photosensor and the fibre.

2.2 INGRID

The INGRID detector consists of 16 identical iron and plastic scintillator detector modules. Each module is constructed of 11 tracking plastic scintillator planes interleaved with 9 passive iron plates, as shown in figure 7 (the final pair of scintillator planes lacks an interleaved iron plate). Each scintillator plane lies perpendicular to the beam direction and consists of 24 horizontally (X) orientated bars glued to a further 24 vertically (Y) orientated bars. Each bar is 1203 mm long and has a cross section of 50×10 mm².

In common with the PØD and ECal scintillator bars, the INGRID bars were produced at Fermilab in 2007–2008. As such they have the same material composition of Dow Styron 663 W polystyrene, doped with 1% PPO and 0.03% POPOP, and co-extruded with a TiO₂ rich material to allow diffuse reflection of scintillation light. Unglued Kuraray Y11(200) M-type WLS fibres collect the light from the bars and are coupled on one end to MPPCs as shown in figure 8. The uninstrumented ends of the bars and fibres are painted with a reflective coating of ELJEN[®] EJ-510.

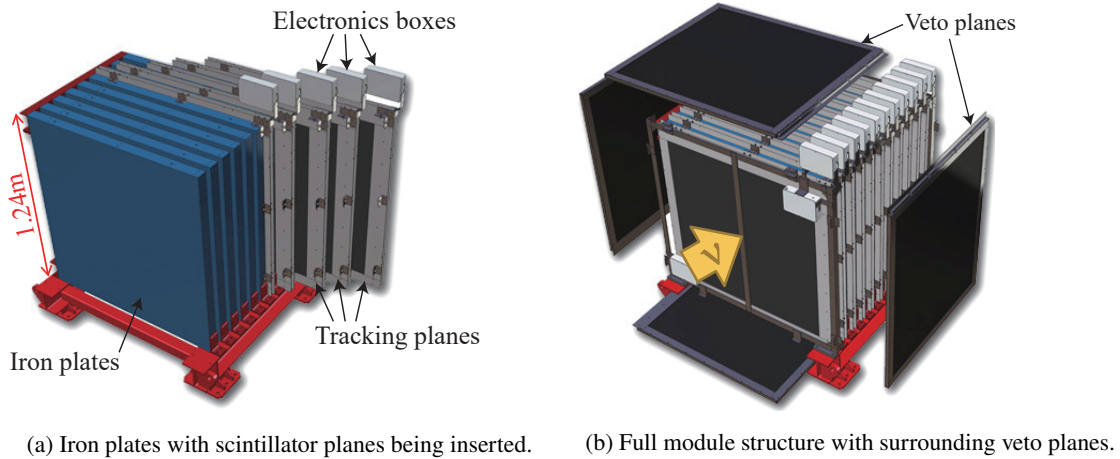


Figure 7: Structure of an INGRID module. Scintillator tracking planes are interleaved with iron plates (a). The sides of the module are then surrounded by scintillator veto planes (b).

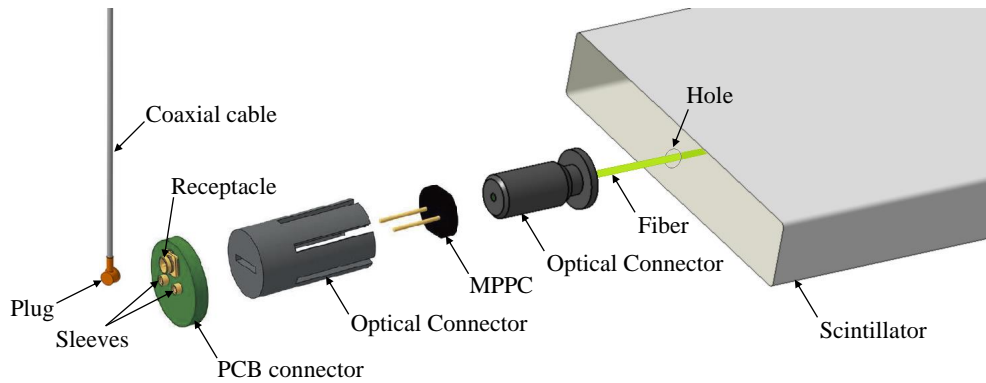


Figure 8: Schematic view of the readout components for INGRID.

The design of the fibre-MPPC coupling for INGRID is the same as used in the FGDs.

3 Light Yield Measurements

The degradation in scintillator response can be quantified by measuring the change over time of the average light yield observed from the passage of minimum ionizing particles (MIP), through the ND280 and INGRID subsystems. The recorded and calibrated response of an MPPC due to the passage of a MIP through a scintillator bar constitutes a “hit” within a subsystem.

Due to the varying geometry and acceptance of the subsystems, several different MIP samples were used for the analysis: beam neutrino interactions, cosmic ray muons recorded concurrently with each T2K Run, or sand muon data (muons produced in neutrino interactions upstream of the detectors).

In all cases the MIP light yield was corrected to account for the length of the MIP’s path through the scintillator bar based on the track angle, and attenuation in the WLS fibre based on the reconstructed position along the scintillator bar.

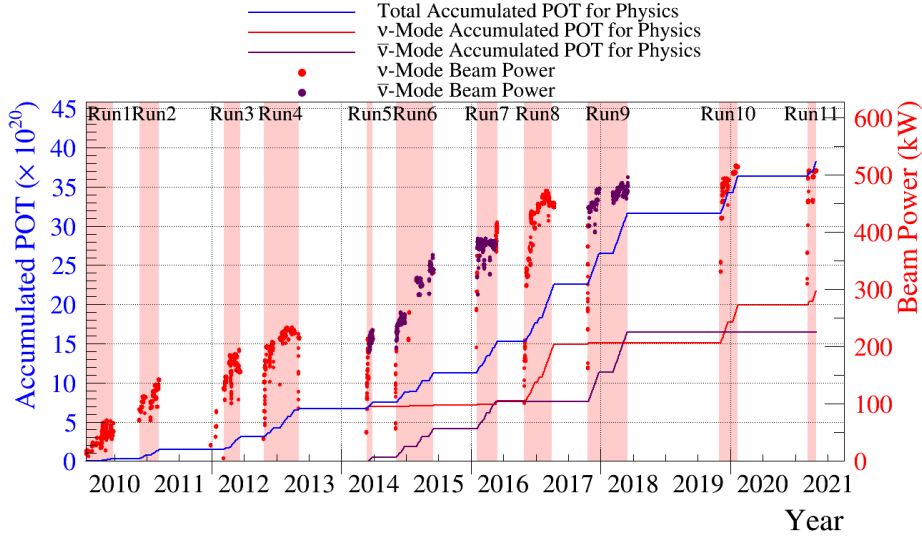


Figure 9: T2K Run periods, associated beam power and accumulated protons on target (POT).

Regular (\sim weekly) adjustments were made to the MPPC overvoltage to account for temperature variations in order to maintain a stable gain, and therefore detector response, over time. This was achieved by stepping through a range of bias voltages and measuring the difference (gain) between the pedestal and single photoelectron response for each MPPC. The correlation between measured gain as a function of voltage was used to extract the appropriate overvoltage to be applied to each MPPC. For ND280 this is supplemented by more frequent calibrations (\sim 3 hourly) that are derived from the recorded detector temperature (FGD) or directly from the pedestal and single photoelectron response of the MPPCs (ECal, SMRD, PØD) and applied during offline reconstruction. Additional empirically derived corrections were also applied to account for the changes in photodetection efficiency, cross talk and after-pulsing as a function of overvoltage [26, 27]. INGRID only uses the pedestal and gain measured after the weekly MPPC bias voltage adjustments for their calibration without additional offline fine-tuning.

3.1 Data Samples

T2K first became operational in March 2010 and neutrino beam data had been recorded during 11 separate T2K Run periods by the end of 2021, as shown in figure 9 and table 2. Data taken during T2K Runs 1–11 and 1–9 were used by the INGRID and ND280 subsystems, respectively, in the analyses described by this paper.

3.2 ND280

For all subsystems within ND280, the MPPC response (hits) for MIP-like tracks measured during each T2K Run were combined to create histograms of accumulated charge per unit length. These histograms were then fitted with the convolution of a Gaussian distribution and a Landau distribution [29], see figure 10. This distribution models the typical energy loss of high-energy particles in matter, along with a Gaussian term to account for detector smearing effects.

Table 2: Dates of T2K Run periods.

T2K Run	Data Taking Period
Run 1	March 2010 – June 2010
Run 2	November 2010 – March 2011
Run 3	February 2012 – June 2012
Run 4	October 2012 – May 2013
Run 5	May 2014 – June 2014
Run 6	November 2014 – June 2015
Run 7	February 2016 – May 2016
Run 8	October 2016 – April 2017
Run 9	October 2017 – May 2018
Run10	November 2019 – February 2020
Run11	March 2021 – April 2021

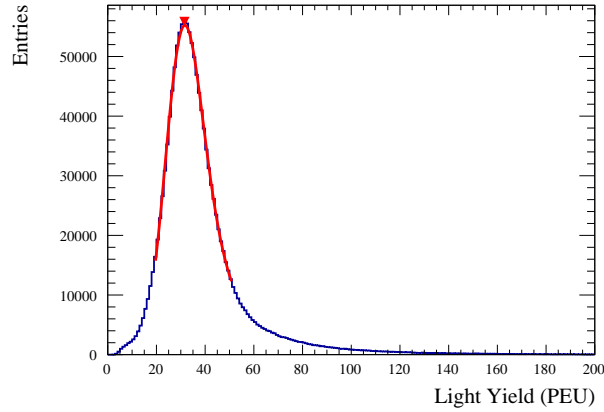


Figure 10: Example MIP light yield distribution in ECal Barrel X after calibrations and corrections are applied. The MIP most probable value (MPV) in Pixel Equivalent Units (PEU) is extracted from a Landau-Gaussian fit to the distribution. A PEU corresponds to the signal of a single MPPC pixel.

The MIP light yield is taken to be the most probable value (MPV) of the Landau-Gaussian fit function. Calibrations designed to maintain the light yield over time, and therefore account for any ageing of the scintillator, are disabled.

Different MIP track selection criteria were developed for each subsystem, dependent upon the detector geometry and chosen data sample, as described below.

3.2.1 PØD

The PØD detector uses a sand muon data sample to monitor the scintillator response. This control sample is selected in the following way:

1. There is only one 3D track reconstructed within the PØD during the beam trigger readout window,
2. This track passes through the first and the last PØDule,

3. Track angle with respect to the beam direction, θ , fulfils the following condition: $\cos \theta \geq 0.8$ (forward going, as measured at the upstream face of the PØD).

These criteria select a sample of MIPs travelling through the detector, leaving hits with well measured 3D positions. The light yield per unit path length for each individual hit is aggregated for each T2K Run separately for each of the four Super-PØDules.

3.2.2 FGD

The FGD (as the PØD) uses a sand muon data sample to monitor the scintillator response. This control sample only includes events where there is just one 3D track reconstructed within each FGD during the beam trigger readout window. The light yield per unit path length for each individual hit is aggregated together for both FGDs for each T2K Run.

3.2.3 ECal

During normal detector operation, high statistic samples of cosmic ray muons traversing the ND280 ECals are routinely recorded. These provide an ideal sample by which to monitor and calibrate the response of the detector modules.

The cosmic ray trigger requires the coincidence of hits to occur within two outer regions on opposite sides of the ND280 detector, outside of the time window used for neutrino beam triggers. These hits can occur within the SMRD, Downstream ECal and most upstream Super-PØDule and indicate that a cosmic ray has traversed ND280. The MIP tracks are then individually reconstructed in 3D using a linear fitting algorithm, with the hits required to have recorded a valid charge and have adjacent hits in each 2D view, see figure 11. The calibrated light yield on each bar is then obtained and can be normalised to account for the angle of incidence of the MIP with respect to the scintillator bar, and optionally the attenuation of the scintillation light as it propagates through the WLS fibre to the MPPC. The attenuation correction normalises the response of interactions at any position along the bar to the response observed at 1 m from the MPPC.

The measured light yield of individual MIP interactions are aggregated for each month or T2K Run separately for the different bar lengths described in section 2.1.3. The analysis presented here uses a random sampling of 5% of all ND280 subruns (the data recorded during ~20 minutes of nominal ND280 operation) from each T2K Run to give excellent statistical coverage over all periods of interest. The 3D reconstruction of the MIP tracks also allows for the hits to be aggregated at different positions along the length of the bars, and when the attenuation length correction is disabled allows the light yield to be measured as a function of distance to the MPPC, which is required for the additional studies described in section 6.

3.2.4 SMRD

For the SMRD both beam and cosmic data samples can be used. However, in most ND280 cosmic trigger configurations the SMRD is not uniformly sampled, leaving some regions statistically limited, unlike in the case of the beam mode triggers. Moreover, only a fraction of the recorded cosmic data sample gets processed. Hence the current study was performed using the beam data sample. The track selection requires:

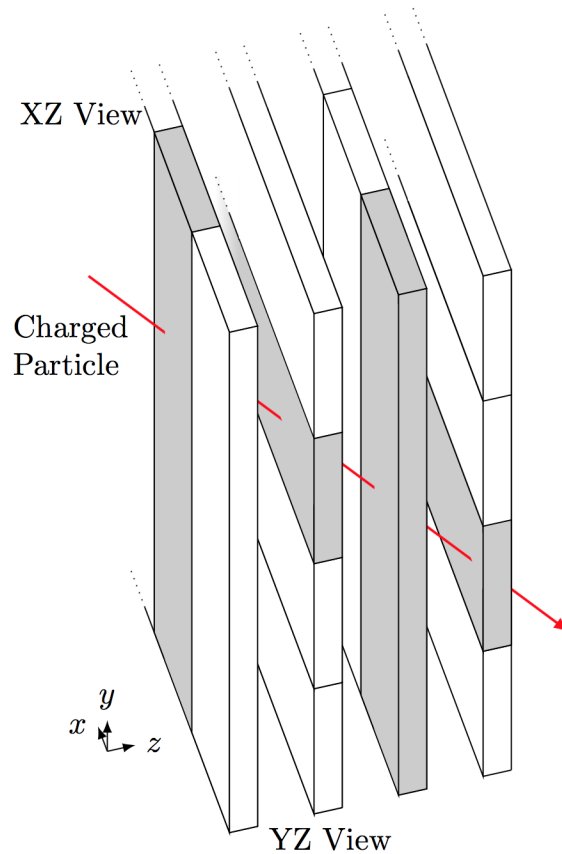


Figure 11: Schematic view of the passage of a MIP through the Downstream ECal module.


1. The highest momentum track reconstructed within the beam trigger readout window has an interaction vertex within the SMRD fiducial volume,
2. The track crosses at least one TPC,
3. The track particle identification hypothesis is consistent with being muon-like.

The light yield per unit path length for each individual SMRD hit is aggregated together for each T2K Run.

3.3 INGRID

INGRID uses a high statistics sample of cosmic ray muons to measure the MIP response of the scintillator bars. The recording of cosmic ray muons is triggered when hits are observed near-simultaneously in four scintillator planes of an INGRID module, outside of the neutrino beam trigger timing window. Channels with more than 2.5 PEU (Pixel Equivalent Units) are defined as hits, and 3D track reconstruction from the hits allows for the recorded MIP response to be corrected for the particle's trajectory through the module.

The INGRID working group has independently assessed the scintillator ageing of the INGRID detector using a different, but equally valid method. Unlike the Landau-Gaussian fitting method employed by the ND280 subsystems, during each J-PARC Main Ring Run (the period between

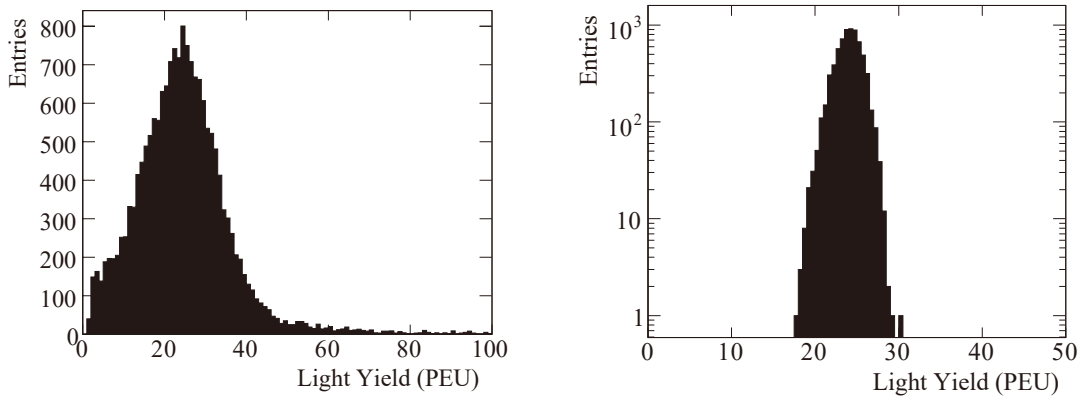

(a) Light yield response of a single channel.

(b) Mean light yield for all channels.

Figure 12: The typical response of a single readout channel (a) and aggregated mean light yield of all channels (b) for INGRID.

each exchange of the H^- ion source, typically one month) the MIP response distribution of each INGRID readout channel is aggregated and the mean response is extracted, see figure 12a. The mean response of all channels are then aggregated, see figure 12b, and the mean of that distribution, the mean-of-means (MOM), is tracked in time to monitor the annual decline in light yield.

3.4 Light Yield Stability Uncertainty

During each data aggregation period (time bin) the measured light yield will vary with time due to changes in the stability of the MPPC response, for example due to overvoltage fluctuations caused by changes in ambient temperature. Such fluctuations affect not only the gain but also the photon detection efficiency. Every effort is made to measure and calibrate out these variations, however this is an imperfect process. Therefore, each subsystem attempts to measure the inherent variation in light yield response within each time bin, and then includes that variation as a systematic uncertainty on the ND280 subsystem MIP MPV or INGRID MOM.

This light yield stability uncertainty is combined in quadrature with the uncertainty of the ND280 MIP MPV from the standard Landau-Gaussian convolution fit or INGRID MOM.

3.4.1 ND280

For all ND280 subsystems, to assess the light yield stability within each time bin, the contributing data samples were split into shorter (reduced) time periods. Within each reduced time period, the MIP response was fitted with the Landau-Gaussian convolution, and the MIP MPV extracted. For each time bin, the standard deviation of the MIP MPVs for the contributing reduced time periods was calculated and taken as the light yield stability uncertainty.

Due to the variation in event rates for the samples used in the MIP MPV estimation for the different ND280 subsystems, the length of the reduced time periods varies between the subsystems to ensure a good balance between temporal granularity and obtaining sufficient statistics to perform an accurate Landau-Gaussian fit. For the ECal, the high statistics of the cosmic ray sample allows

Table 3: Absolute range and modal light yield stability uncertainties in PEU for each subsystem. Also shown are the range and modal uncertainties as a percentage of the recorded MPV in each time bin.

Subsystem	Uncertainty Range		Modal Uncertainty	
	Absolute Value (PEU)	% of MPV	Absolute Value (PEU)	% of MPV
PØD	0.02–0.57	0.11–2.57	~0.20	~0.90
ECal (Single-ended)	0.07–2.19	0.28–8.24	~0.15	~0.80
ECal (Double-ended)	0.05–1.22	0.33–7.35	~0.10	~0.90
FGD	0.10–0.29	0.51–1.33	~0.15	~0.70
SMRD	0.79–1.33	1.4–2.3	1.33	2.3
INGRID	0.07–0.74	0.30–3.28	~0.30	~1.50

data to be aggregated into periods of ~20 minute duration (the period of one ND280 subrun), however for the FGD and PØD, the slower event rate of sand muon data means the data was aggregated into periods of one-month and two-weeks, respectively. For the SMRD, the T2K Runs with the highest statistics were studied and the data was aggregated into one week periods. The largest standard deviation, among the T2K Runs, was then taken as the error to be conservatively applied to all SMRD data points. The range of uncertainties, and modal uncertainty, across all data periods are shown in table 3. Most uncertainty values lie close to modal value, with a few exceptions which push out the maximum range to higher values.

3.4.2 INGRID

INGRID takes a similar approach to the ND280 subsystems, aggregating the cosmic ray data over 3 day periods and extracting the standard deviation in the MOM extracted from those reduced periods. This provides uncertainties of 0.3-3.3% in each time bin.


4 Annual Light Yield Reduction

The distribution of the ND280 MIP MPV or INGRID MOM was extracted for each subsystem during each T2K Run and then fitted with a linear function in order to calculate the overall drop in light yield and annual decrements, see figure 13.


The data is aggregated by T2K Run for the PØD, FGD and SMRD, with the time error being the standard deviation in time stamp of all MIP hits during each T2K Run. For the ECal and INGRID, the higher statistic allows for the data to be instead aggregated on a per month basis, or per J-PARC Main Ring Run, respectively. The fit is only applied to the data from January 2012 (December 2010) onwards for the ND280 (INGRID) subsystems as the current calibration procedures and cosmic ray triggering prescale were not finalised until that time.

As described in the previous section, for the PØD and ECal subsystems (see sections 3.2.1 and 3.2.3 respectively) the study has been performed for all sub-modules or bar types separately, see figures 13a and 13b.


The reduction in light yield extracted by the described method measures the loss in performance of the whole readout system; the scintillator, WLS fibre, MPPC and their couplings. However it is

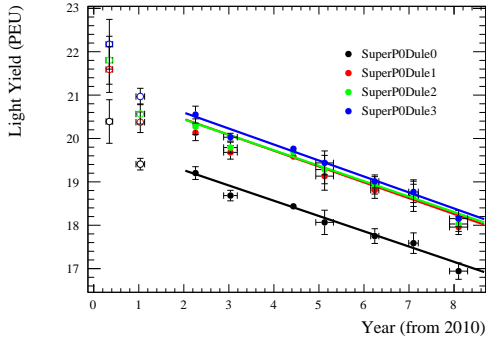


(a) PØD.

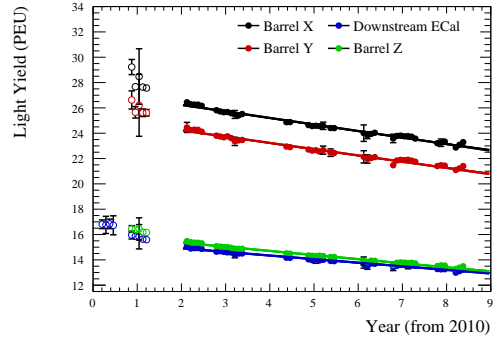


(b) ECal.

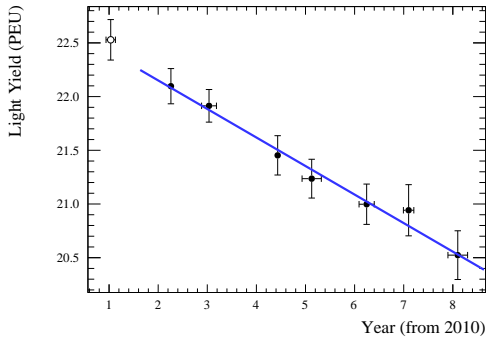

(c) FGD.

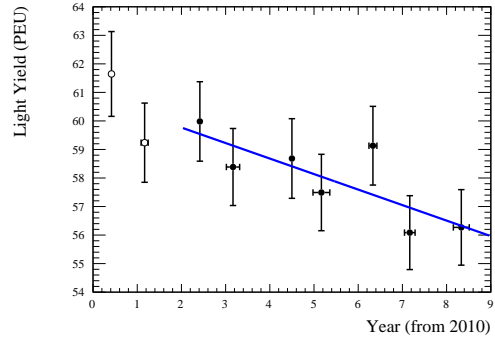

(d) SMRD.

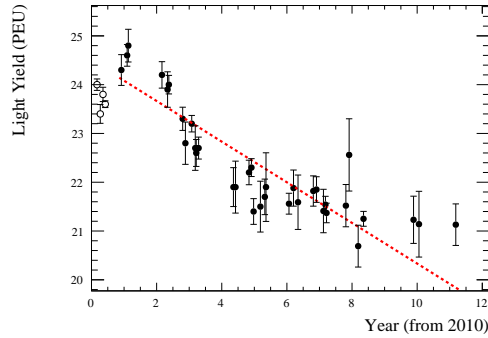

(e) INGRID.

Figure 13: Light yield change in each subsystem for T2K Runs 3–9 (ND280) and Runs 2–11 (INGRID). The x-error bars (time) show the standard deviation in the hit times for each data aggregation period, and the y-error bars (light yield) show the quadratic sum of the light yield stability uncertainty and the uncertainty on the ND280 Landau-Gaussian MIP MPV or INGRID MOM. Hollow data points are excluded from the data fits.

Table 4: Linear fit parameters to PØD, FGD, SMRD, ECal and INGRID data from figure 13 and the annual percentage reduction, relative to the 2012 fit values. Single-ended readout bars are mirrored on one end.

Subsystem	Readout Type	A (PEU)	B (PEU/yr)	χ^2/NDF	Annual Reduction (%)
Super-PØDule 0	Single-ended	19.97 ± 0.15	0.35 ± 0.03	4.35/5 = 0.87	1.82 ± 0.16
Super-PØDule 1	Single-ended	21.17 ± 0.16	0.36 ± 0.04	10.39/5 = 2.08	1.76 ± 0.20
Super-PØDule 2	Single-ended	21.15 ± 0.17	0.36 ± 0.03	9.14/5 = 1.83	1.76 ± 0.15
Super-PØDule 3	Single-ended	21.33 ± 0.16	0.37 ± 0.03	5.46/5 = 1.09	1.80 ± 0.15
FGD	Single-ended	22.68 ± 0.19	0.27 ± 0.04	0.74/5 = 0.15	1.22 ± 0.18
SMRD	Double-ended	60.86 ± 1.48	0.54 ± 0.26	2.62/5 = 0.52	0.90 ± 0.44
ECal Barrel X	Single-ended	27.27 ± 0.06	0.52 ± 0.01	33.09/37 = 0.89	1.98 ± 0.04
ECal Barrel Y	Single-ended	25.21 ± 0.08	0.49 ± 0.01	31.88/37 = 0.86	2.02 ± 0.04
ECal Barrel Z	Double-ended	16.01 ± 0.04	0.33 ± 0.01	36.60/37 = 0.99	2.15 ± 0.07
Downstream ECal	Double-ended	15.48 ± 0.06	0.28 ± 0.01	11.57/37 = 0.31	1.87 ± 0.07
INGRID	Single-ended	24.50 ± 0.11	0.42 ± 0.02	89.32/33 = 2.71	1.78 ± 0.08

assumed that the bulk of the light yield reduction can be ascribed to the degradation of the plastic scintillator as this is a well known phenomenon (as described in section 1.2), and there has been no obvious degradation in MPPC performance (for example significant drift in overvoltage settings with time), and the stability of the WLS fibre will be addressed in section 6.

Without knowledge of the ageing mechanism(s) degrading ND280 and INGRID subsystems it is difficult to know what form the time dependence on the ageing rate should be expected to take. A priori it might be expected that an exponential function would be suitable, and fits of this form are used for projecting the future response of the most important subsystems in section 5. However, given the observed data distributions and timescale studied a simple linear fit is found to be appropriate, and are applied in the form:

$$f(t) = A - Bt, \quad (4.1)$$

where A is the fitted light yield in PEU at year 0 (2010), B is the gradient of the fit in PEU per year, and t is the year since 2010. The fit parameters are shown in table 4.

The degradation of the scintillator appears to be reasonably consistent across all subsystems. All show a reduction in light yield within the range ~0.3–0.5 PEU per year, equivalent to an annual light yield reduction of 0.9–2.2% relative to their 2012 fit values.

The 1% difference separating the highest and lowest degradation rates between the materially identical FGD (1.2%) and ECal (Barrel Z 2.2%), is not surprising given the differences in production dates for the scintillator bars, and the varying environmental conditions they had experienced during their production, transportation, and positioning within ND280. All of the aforementioned factors will have contributed to differences in the temperature, humidity and UV exposure of the bars across their lifetimes, and so impacted upon their respective ageing profiles.

The higher statistics of the ECal allows for a finer assessment of its ageing rate. An initial rapid ageing is observed within the first two years of operation, followed by a near linear reduction beyond 2012, however it is unclear if this is a real effect or just an artefact of the changes in calibration procedure and cosmic ray triggering prescale. The higher ECal light yield obtained by the Barrel X and Y bars is due to the combination of direct and reflected light signals for these single-ended

(mirrored) readout channels, compared to direct transmission only for the double-ended readout of the Barrel Z and Downstream bars.

Results from the MINOS experiment, which uses materially identical bars to the FGD, ECal, PØD and INGRID, showed ageing rates of $\sim 2\%$ per year [10] over 3 and 4.5 year periods measured with their near and far detectors respectively, in good agreement with the higher rates we obtain from the ECal and PØD.

The MINER ν A experiment found a substantially higher rate of ageing for their scintillator bars, equivalent to a $\sim 7.5\%$ annual reduction in light yield over a 2 year study period [11]. It is unclear why MINER ν A measured such a high rate of degradation as their scintillator composition is again identical to that used by MINOS and most T2K subsystems. It might be possible that MINER ν A has sampled an initial rapid ageing of their scintillator, as perhaps indicated in the earliest ECal data points as discussed above, and also anecdotally observed by MINOS [10]; and that further study of later data would show a reduced ageing rate in line with those measured by T2K and MINOS. For completeness, if a linear fit is applied only to the currently excluded Downstream ECal data recorded during the 2010–2011 period, an annual light loss rate of 1.33 ± 0.29 PEU per year on an initial light yield of 17.2 ± 0.3 is obtained. This is equivalent to annual reduction in light yield of $7.7 \pm 1.7\%$ which is in excellent agreement with the MINER ν A result.

5 Projected Future Response

The PØD subsystem of the ND280 is being decommissioned in 2022 to allow for the upgrade of the ND280 detector [30]. The remaining ECal, FGD, SMRD and INGRID subsystems will be retained in their current form, and so an understanding of their future response will become increasingly important as the T2K near detectors continue operating into the T2K-II [31] and the Hyper-Kamiokande [32] eras.

As such the future response of the ECal, FGD and INGRID subsystems has been projected through until 2040. The SMRD is excluded from this study as its initial light yield is substantially higher than for the other subsystems and its rate of degradation is lower. As such the likelihood of the light yield from this subsystem dropping below any reconstruction threshold is not considered to be an issue for the time period considered.

Although a linear fit to the data in section 4 results in a reasonable agreement, an exponential fit is better physically motivated. Figure 14 shows the projected future response from the earlier linear fits, and from the application of an exponential fit to the ECal and FGD data from 2012, and the INGRID data from 2010, onwards. The exponential fit is of the form:

$$f(t) = A \exp\left(\frac{-t}{\tau}\right), \quad (5.1)$$

where A is the fitted light yield in PEU at year 0 (2010), τ is the time constant of the exponent in years, and t is the year since 2010. The fit parameters are shown in table 5.

The time constant τ is consistent, ~ 44 – 49 years, for all ECal bar types, along with the light yield constant A for the pairs of single-ended (mirrored), ~ 26 PEU, and double-ended, ~ 16 PEU, readout bars. The resultant χ^2/NDF for the exponential fits are marginally reduced by ~ 0.1 – 0.2 compared to the corresponding linear fits shown in table 4.

Table 5: Exponential fit parameters to ECal, FGD and INGRID data from figure 14.

ECal Bar Type	Readout Type	A (PEU)	τ (yr)	χ^2/NDF
Barrel X	Single-ended (mirrored)	27.39 ± 0.07	47.7 ± 1.1	$27.82/37 = 0.75$
Barrel Y	Single-ended (mirrored)	25.34 ± 0.08	45.7 ± 1.3	$28.27/37 = 0.76$
Barrel Z	Double-ended	16.10 ± 0.04	44.1 ± 0.9	$29.64/37 = 0.80$
Downstream	Double-ended	15.55 ± 0.07	49.2 ± 2.6	$10.28/37 = 0.28$
FGD	Single-ended (mirrored)	22.72 ± 0.20	80.3 ± 11.1	$0.68/5 = 0.14$
INGRID	Single-ended (mirrored)	24.61 ± 0.11	52.9 ± 2.4	$82.27/33 = 2.49$

The INGRID time constant of 52.9 ± 2.4 years is marginally longer than those recorded by the ECal, and the resultant χ^2/NDF for the exponential fit has slightly reduced by 0.22. The FGD records a significantly longer time constant of 80.3 ± 11.1 years and a negligible increase of 0.01 in its χ^2/NDF for the exponential fit compared to the linear fit. As with the linear ageing results (see table 4), some variation in the degradation rates between the different subsystems is expected due to the varying age and environmental exposure profiles of the scintillator bars, although why the FGD should be such an outlier is unclear.


The anticipated ECal response drops by $\sim 50\%$ or $\sim 60\%$ over thirty years for all bar types from extrapolations of the exponential and linear fits, respectively. This remains above the minimum charge threshold of 5.5 PEU required for use in the current ECal offline reconstruction algorithms. The value of this threshold has been chosen to avoid discrepancies between data and the current MC simulation at low charges. It should be possible to lower the current charge threshold through more detailed simulation of the detector response, for example including bar non-uniformity and improved MPPC dark-noise rate, and through enhancing the reconstruction algorithms. Without improvement there is a risk that information will be lost for particle interactions which deposit energy at values below the MIP MPV, potentially limiting the physics reach of analyses which utilise the ECal.

The FGD and INGRID subsystems expect their MIP MPV or MOM response to reduce by $\sim 30\%$ and $\sim 40\%$, respectively, over thirty years under the hypothesis of an exponential decline. For both detectors this increases by a further $\sim 5\text{-}10\%$ for a linear decline. For both scenarios this remains far above the hit thresholds of 5.0 and 2.5 PEU, respectively, currently used by the offline reconstruction algorithms for these detectors. If the true rate of ageing were to be higher, such as the $\sim 50\text{-}60\%$ light yield reduction currently projected by the ECal, this would still not be a concern for these subsystems.


6 Separation of ECal Scintillator and Fibre Degradation

The results shown in section 4 combines the ageing of the scintillator bars with that of the WLS fibres¹, therefore a second approach was applied to separate the two effects within the ECal data. Without applying the attenuation correction, the MIP MPV response is extracted at different distances from the sensor for each bar type during each T2K Run, see figure 15.


¹Any degradation of the coupling between the fibre and the MPPC, either through loss of transparency of the epoxy or gradual displacement of the fibre also contributes to the results.

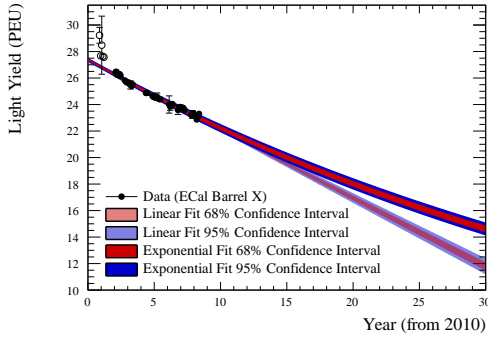


(a) ECal Barrel X.

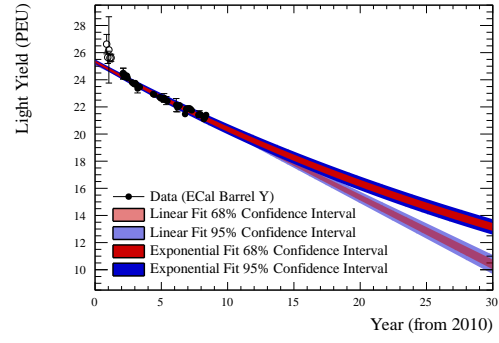


(b) ECal Barrel Y.

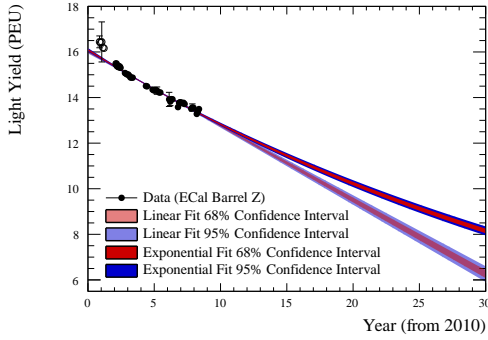


(c) ECal Barrel Z.

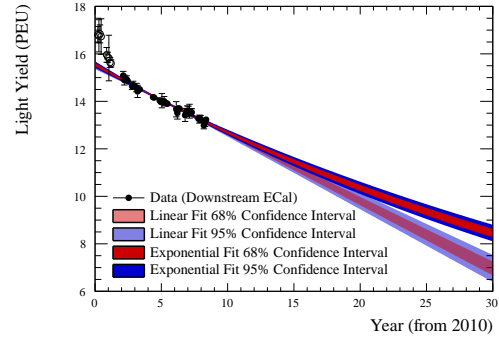

(d) Downstream ECal.

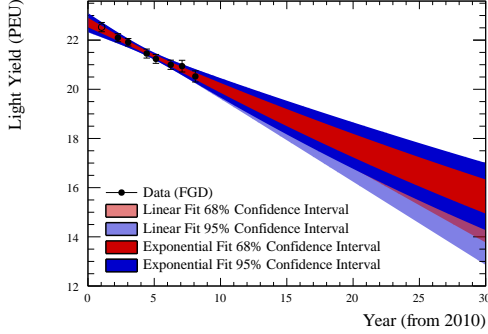

(e) FGD.

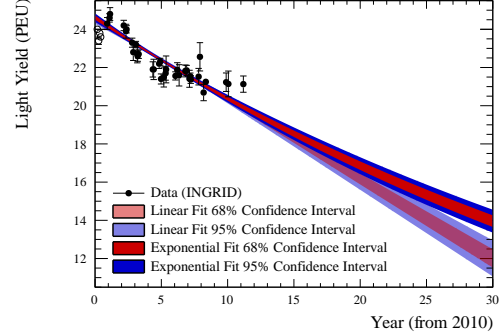

(f) INGRID.

Figure 14: Projected light yield for each ECal bar type, FGD and INGRID, showing the 68% and 95% confidence intervals extracted from both the linear and exponential fits to the data. Hollow data points are excluded from the data fits.

The best fit to the data was achieved by applying a double-exponential fit, which accounts for the short and long components of the fibre attenuation, of the form:

$$f(x) = S \exp\left(\frac{-x}{\lambda_S}\right) + L \exp\left(\frac{-x}{\lambda_L}\right), \quad (6.1)$$

where S and L are the fitted light yield in PEU at 0 cm from the MPPC for the short and long

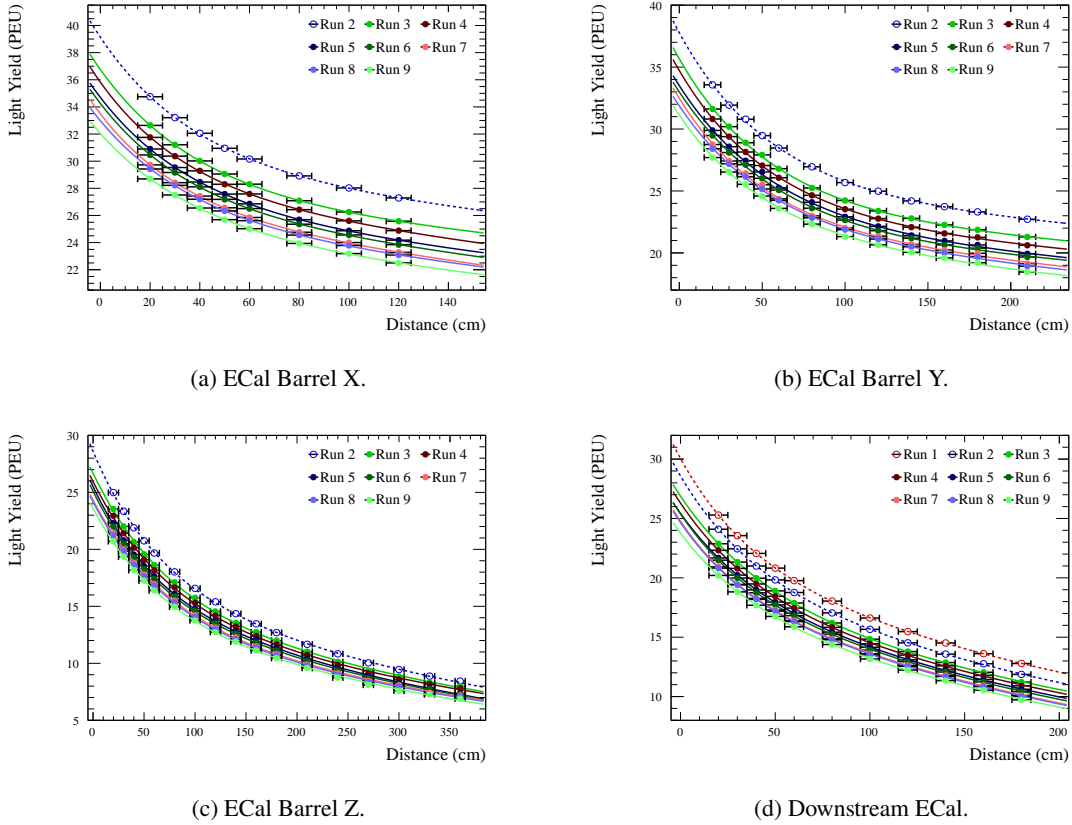


Figure 15: ECal light yield as a function of distance to the MPPC for each T2K Run. The errors on the data points are only the uncertainty on the Landau-Gaussian fit MPV at each distance point, no light yield stability uncertainty is applied. Results of the fits to the hollow data points are excluded from the subsequent data fits.

components of the exponential function, respectively; λ_S and λ_L are the associated short and long attenuation lengths; and x is the distance from the MPPC in cm.

6.1 Scintillator Degradation

The parameters of the double-exponential fits can be used to calculate the predicted total MIP light yield at a distance of 0 cm from the MPPC, $S + L$. This should remove the dependence on the propagation of the light down the WLS fibre and the decrease in evaluated light yield will only be dependent on the ageing of the scintillator. The results for this evaluation are shown in figure 16 with both a linear and exponential fit applied to the data from 2012.

The linear fit is of the form:

$$f(t) = A - Bt, \quad (6.2)$$

where A is the fitted total MIP light yield ($S + L$) in PEU at year 0 (2010), B is the gradient of the fit in PEU per year, and t is the time in years since 2010. The fit parameters are shown in table 6.

For the single-ended (mirrored) readout bars the reduction in light yield from the scintillator ageing is ~ 0.75 PEU per year, and for the double-ended readout bars it is ~ 0.50 PEU per year.

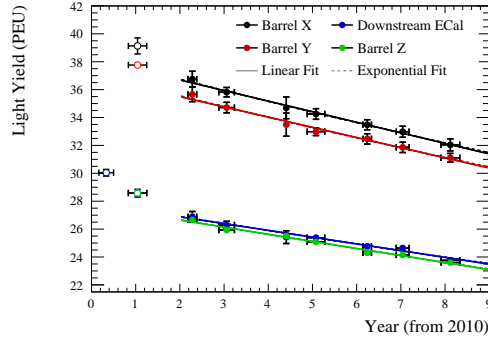


Figure 16: Light yield as evaluated at 0 cm from the MPPC for each ECal bar type. Hollow data points are excluded from the data fits.

Table 6: Linear fit parameters to ECal light yield at 0 cm from the MPPC from figure 16, and annual percentage reduction in light yield, relative to 2012 fit value. Reference results, in parentheses, from the linear fit in table 4 are included for comparison

ECal Bar Type	Readout Type	A (PEU)	B (PEU/yr)	χ^2/NDF	Annual Reduction (Ref.) (%)
Barrel X	Single-ended	38.21 ± 0.50	0.76 ± 0.09	$0.45/5 = 0.09$	2.07 ± 0.25 (1.98 ± 0.04)
Barrel Y	Single-ended	36.94 ± 0.47	0.73 ± 0.08	$1.40/5 = 0.28$	2.06 ± 0.23 (2.02 ± 0.05)
Barrel Z	Double-ended	27.65 ± 0.18	0.50 ± 0.03	$3.66/5 = 0.73$	1.88 ± 0.11 (2.15 ± 0.07)
Downstream	Double-ended	27.87 ± 0.32	0.49 ± 0.05	$2.69/5 = 0.54$	1.82 ± 0.18 (1.87 ± 0.07)

Table 7: Exponential fit parameters to ECal light yield at 0 cm from the MPPC from figure 16. Reference time constants, in parentheses, from the exponential fit in table 5 are included for comparison.

ECal Bar Type	Readout Type	A (PEU)	τ (Ref.) (yr)	χ^2/NDF
Barrel X	Single-ended	38.4 ± 0.5	45.2 ± 5.1 (47.7 ± 1.1)	$0.37/5 = 0.07$
Barrel Y	Single-ended	37.2 ± 0.5	45.2 ± 4.8 (45.7 ± 1.3)	$1.11/5 = 0.22$
Barrel Z	Double-ended	27.8 ± 0.02	49.5 ± 3.0 (44.1 ± 0.9)	$3.22/5 = 0.64$
Downstream	Double-ended	28.0 ± 0.3	51.6 ± 5.3 (49.2 ± 2.6)	$2.82/5 = 0.56$

This is a reduction of $\sim 2.1\%$ for the single-ended (mirrored) bars, and $\sim 1.9\%$ per year for the double-ended bars.

The exponential fit is of the form:

$$f(t) = A \exp\left(\frac{-t}{\tau}\right), \quad (6.3)$$

where A is the fitted total MIP light yield ($S + L$) in PEU at year 0 (2010), τ is the time constant of the exponent in years, and t is the year since 2010. The fit parameters are shown in table 7.

For the linear fits the annual reduction in light yield is consistent within $\sim 1\sigma$ of the reference degradation shown in table 4, and similarly the time constant for the exponential fits is consistent within $\sim 1\sigma$ of the reference values shown in table 5. This suggests the ageing is dominated by the degradation of the scintillator rather than the WLS fibres.

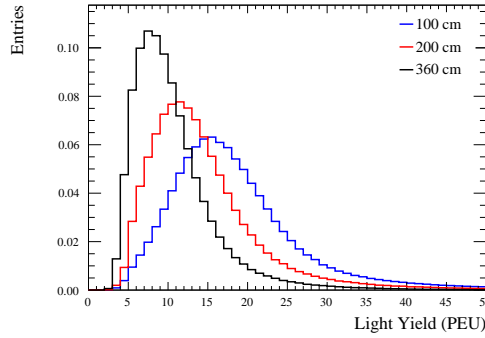


Figure 17: MIP light yield distribution in the ECal Barrel Z bars during T2K Run 9, for cosmic rays passing at distances of 100, 200 and 360 cm from the MPPCs.

The exception to this is the Barrel Z results which lie $\sim 2\sigma$ from the reference values and imply a slower rate of degradation than those shown in the earlier results of section 4 and 5. This is likely due to some loss in MIP hit efficiency at the furthest distances from the MPPCs as the scintillator degrades. This would truncate the rising edge of the MIP light yield distribution, see for example at a distance of 360 cm in figure 17, shifting the extracted MIP MPV to a slightly higher value than might be otherwise expected. The result would be an underestimate in the degradation rate extracted with this technique for the Barrel Z bars, leading to the discrepancy when making comparisons with the reference values.

Fortunately any loss in hit efficiency at the furthest distances from the MPPCs will have negligible impact on the overall hit reconstruction efficiency as the MPPC on the opposing end of the bars will continue to efficiently reconstruct these hits, as only one MPPC is required to reconstruct a hit on the double-ended readout bars.

This is confirmed by separate studies monitoring hit efficiency in the ECal modules which observed a negligible reduction ($\sim 0.1\%$) in the single-hit efficiency (requiring a hit in the single-ended readout bars, or at least one hit on either end of the double-ended readout bars) across all bar types during the current lifetime of the ECal. For the double-end readout bars the double-hit efficiency (requiring a hit on both ends of a scintillator bar) has reduced by $\sim 2\%$ over the current lifetime.

In the future there may be some concern regarding the reconstruction of hits at the centre of the Barrel Z bars, where hits are equidistant from both sensors, and so where any impact on reconstruction efficiency will first become apparent. However, this is not a concern for the current data as shown by the MIP light yield distribution at a distance of 200 cm in figure 17, but will need to be monitored.

6.2 Fibre Degradation

Along with extracting the light yield from the fits in figure 15, it is also possible to study the change in the short and long attenuation length components of the double-exponential fit, λ_S and λ_L , respectively, for the WLS fibres. These are shown in figure 18 with linear fits applied to the

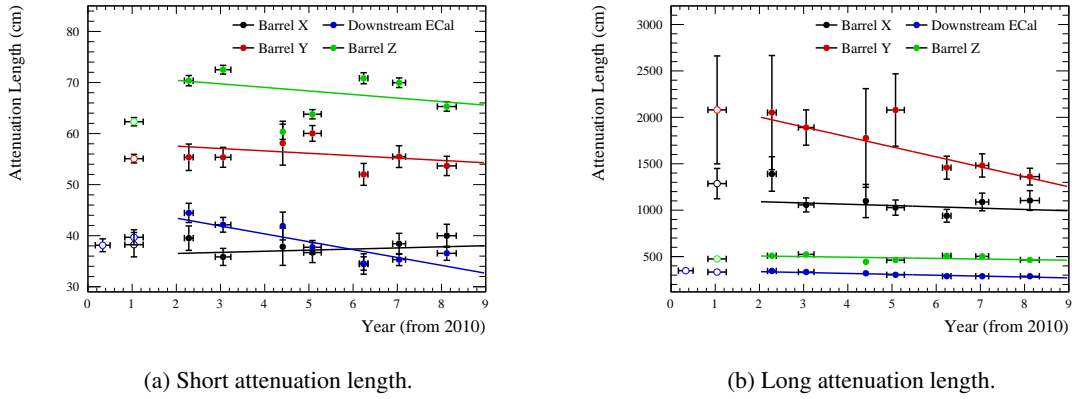


Figure 18: Short and long attenuation lengths, λ_S and λ_L respectively, from equation 6.1. Hollow data points are excluded from the data fits. Note the suppressed 0 for the ordinate of figure 18a.

Table 8: Linear fit parameters to ECal short and long attenuation length components of double-exponential fits from figure 18, and the annual percentage reduction, relative to 2012 fit values.

		Short Attenuation Length Component			
ECal Bar Type	Readout Type	λ_S (0) (cm)	k_S (cm/yr)	χ^2/NDF	Annual Reduction (%)
Barrel X	Single-ended	36.1 ± 2.3	-0.22 ± 0.41	5.21/5 = 1.04	-0.60 ± 1.12
Barrel Y	Single-ended	58.5 ± 2.4	0.47 ± 0.42	11.10/5 = 2.22	0.82 ± 0.73
Barrel Z	Double-ended	71.8 ± 1.1	0.70 ± 0.19	87.16/5 = 17.43	0.99 ± 0.27
Downstream	Double-ended	46.4 ± 1.8	1.52 ± 0.29	8.48/5 = 1.70	3.51 ± 0.69
		Long Attenuation Length Component			
ECal Bar Type	Readout Type	λ_L (0) (cm)	k_L (cm/yr)	χ^2/NDF	Annual Reduction (%)
Barrel X	Single-ended	1119 ± 117	13.9 ± 19.8	5.98/5 = 1.20	1.27 ± 1.82
Barrel Y	Single-ended	2218 ± 262	107.2 ± 35.6	1.68/5 = 0.34	5.35 ± 1.92
Barrel Z	Double-ended	520 ± 6	6.6 ± 1.1	146.47/5 = 29.29	1.30 ± 0.22
Downstream	Double-ended	354 ± 7	9.1 ± 1.1	13.29/5 = 2.67	2.71 ± 0.33

data from 2012 of the form:

$$\lambda_i(t) = \lambda_i(0) - k_i t, \quad (6.4)$$

where $\lambda_i = \{\lambda_S, \lambda_L\}$ is the short or long attenuation length in cm at year 0 (2010), $k_i = \{k_S, k_L\}$ is the gradient of the fit in cm per year, and t is the year since 2010. The fit parameters are shown in table 8.

The short attenuation length varies between 36 and 72 cm, increasing as the bar length increases, and it appears to be consistent with minimally ($< 1\%$) or not degrading with time. The exception to this is the Downstream ECal which shows a higher degradation rate of $3.51 \pm 0.69\%$, although if the earlier Run 1 and 2 data were to be included this would substantially reduce.

For the long attenuation length, the single-ended (mirrored) bars have much longer attenuation lengths compared to the double-ended readout bars, ~ 1120 and ~ 2220 cm for the Barrel X and Y bars, respectively, compared to ~ 520 and ~ 355 cm for the Barrel Z and Downstream bars, respectively. This discrepancy is due to the mirrored bars having two signals, direct transmission down the WLS fibres to the MPPCs, and reflected transmission, the combination of which is not

accounted for in the fits, and so these are not true measurements of the long attenuation length.

For comparison, early fibre scanning work during construction on the ND280 ECals measured short and long attenuation lengths for the WLS fibres in the range 21–31 cm and 390–410 cm, respectively [27].

Kuraray have also measured the attenuation length of their fibres from light yield measurements over a distance range of 100–300 cm, fitting the distribution with a single exponential function and extracting an attenuation length of >350 cm [8], in agreement with our long attenuation length results.

The Mu2e collaboration which also uses Kuraray Y-11 WLS fibres has measured the attenuation length of the fibres, but over substantially longer fibre lengths of 25 m. In a 2015 study they applied a double-exponential fit to their data of the same form shown in equation 6.1 and extracted short and long attenuation lengths of 4.76 and 9.02 m, respectively [33]. A later study in 2018 separated the data into two independent exponential fits over the ranges 0.5–3.0 m and 3.0–25.0 m, and again extracting short and long attenuation lengths, this time of 5.1 ± 0.2 and 8.2 ± 0.1 m, respectively [34]. In both cases their short attenuation length measurement is consistent with the (double-ended readout bars) long attenuation lengths we have obtained. Perhaps of greater interest though are their measurements of attenuation length as a function of wavelength which show very short attenuation lengths of less than 50 cm at 490 nm, approaching the peak quantum efficiency for our MPPCs which occurs at 440 nm [35] (unfortunately the Mu2e measurements do not extend to wavelengths below 490 nm) and longer attenuation lengths of ~400 cm at 510 nm.

Kuraray Y-11 WLS fibres absorb light over wavelengths of ~360–490 nm, and emit between ~460–570 nm [8]. Our two attenuation length measurements can then be readily explained. A short attenuation length attributed to the overlapping absorption and emission regions of the Y-11 WLS fibres around ~475 nm (near the maximum quantum efficiency of the MPPCs), and a longer attenuation length coinciding with the emission only region of the Y-11 WLS fibres at >490 nm (mean emission value of ~510 nm [27]), as corroborated by the single wavelength Mu2e attenuation length measurements.

Irrespective of the mirroring or not, the long attenuation lengths do appear to be degrading by between 1.27% and 5.35% per year, although the single-ended (mirrored) bars have significant uncertainties on those rates.

As to why the long attenuation length would show degradation whilst the short attenuation length does not is unknown. Potentially a wavelength dependent change in the opacity of the fibres has occurred, allowing shorter wavelengths (<490 nm) to propagate in a consistent manner over the current lifetime of the WLS fibres, whilst increasing the opacity to longer wavelengths (>490 nm). However this is purely conjecture and we cannot ascribe a mechanism for such behaviour.

7 Conclusions

The rate of ageing for the different scintillator subsystems of ND280 and INGRID has been studied. The materially identical ECal, PØD, FGD and INGRID observe an annual deterioration in the light yield of 1.2–2.2%, whilst the SMRD shows a somewhat lower rate of degradation at $0.9 \pm 0.4\%$. These results are comparable to similar studies by the MINOS experiment (~2%) [10], but

Table 9: Summary of the annual light yield reduction for ND280 and INGRID subsystems, relative to their 2012 light yields.

Subsystem	Annual Light Yield Reduction (%)
PØD	1.8 ± 0.2
FGD	1.2 ± 0.2
ECal	$(1.9 - 2.2) \pm 0.1$
SMRD	0.9 ± 0.4
INGRID	1.8 ± 0.1

inconsistent with a shorter duration study undertaken by the MINERvA experiment ($\sim 7.5\%$) [11], both of which use scintillator bars which are materially identical to the majority of T2K subsystems.

Modelling the decrease in light yield of the ECal as an exponential shows that the response is expected to halve by 2040, at which time the reduced response may become challenging for some physics analyses. This may be beyond the lifetime of the ND280 detector, but if its use continues into the Hyper-Kamiokande era then it motivates the development of improved detector simulation and reconstruction algorithms to mitigate the impact. The higher initial response and lower degradation rates of the other ND280 subsystems and INGRID implies their physics capabilities are less likely to be negatively impacted over the same timescales.

The additional study to disentangle the degradation of the scintillator and WLS fibres within the ECal shows that the majority of the ageing can be attributed to the degradation of the scintillator rather than the WLS fibres. The short component of the WLS fibre attenuation length appears consistent with not degrading, although the long attenuation component does appear to degrade by between 1–5% per year, and the cause of this apparent discrepancy is unknown.

A summary of the annual light yield reduction for each ND280 scintillator detector can be found in table 9.

Data supporting the results reported in this paper are openly available from the Zendo data repository and can be found here [36].

Acknowledgments

We thank the J-PARC staff for superb accelerator performance. We thank the CERN NA61/SHINE Collaboration for providing valuable particle production data. We acknowledge the support of MEXT, JSPS KAKENHI (JP16H06288, JP18K03682, JP18H03701, JP18H05537, JP19J01119, JP19J22440, JP19J22258, JP20H00162, JP20H00149, JP20J20304) and bilateral programs (JPJSBP120204806, JPJSBP120209601), Japan; NSERC, the NRC, and CFI, Canada; the CEA and CNRS/IN2P3, France; the DFG (RO 3625/2), Germany; the INFN, Italy; the Ministry of Education and Science(DIR/WK/2017/05) and the National Science Centre (UMO-2018/30/E/ST2/00441), Poland; the RSF19-12-00325, RSF22-12-00358 and the Ministry of Science and Higher Education (075-15-2020-778), Russia; MICINN (SEV-2016-0588, PID2019-107564GB-I00, PGC2018-099388-BI00) and ERDF funds and CERCA program, Spain; the SNSF and SERI (200021_185012, 200020_188533, 20FL21_186178I), Switzerland; the STFC, UK; and the DOE, USA. We also thank CERN for the UA1/NOMAD magnet, DESY for the HERA-B magnet mover system, NII

for SINET5, the WestGrid and SciNet consortia in Compute Canada, and GridPP in the United Kingdom. In addition, the participation of individual researchers and institutions has been further supported by funds from the ERC (FP7), “la Caixa” Foundation (ID 100010434, fellowship code LCF/BQ/IN17/11620050), the European Union’s Horizon 2020 Research and Innovation Programme under the Marie Skłodowska-Curie grant agreement numbers 713673 and 754496, and H2020 grant numbers RISE-GA822070-JENNIFER2 2020 and RISE-GA872549-SK2HK; the JSPS, Japan; the Royal Society, UK; French ANR grant number ANR-19-CE31-0001; and the DOE Early Career programme, USA.

References

- [1] K. Abe *et al.*, “The T2K experiment,” *Nuclear Instruments and Methods in Physics Research Section A: Accelerators, Spectrometers, Detectors and Associated Equipment*, vol. 659, no. 1, pp. 106–135, 2011.
- [2] T. Koseki *et al.*, “Beam commissioning and operation of the J-PARC main ring synchrotron,” *Progress of Theoretical and Experimental Physics*, vol. 2012, 12 2012. 02B004.
- [3] S. Fukuda *et al.*, “The Super-Kamiokande detector,” *Nuclear Instruments and Methods in Physics Research Section A: Accelerators, Spectrometers, Detectors and Associated Equipment*, vol. 501, no. 2, pp. 418–462, 2003.
- [4] “ND280 technical design report.” <http://www.nd280.org/convenors/ND280%20Review%20document%202006/tdr.pdf>, 2006.
- [5] K. Abe *et al.*, “Measurements of the T2K neutrino beam properties using the INGRID on-axis near detector,” *Nucl. Instrum. Meth. A*, vol. 694, pp. 211–223, 2012.
- [6] B. Quilain and A. Minamino, “The WAGASCI detector as an off-axis near detector of the T2K and Hyper-Kamiokande experiments,” *Journal of Physics: Conference Series*, vol. 888, p. 012166, 9 2017.
- [7] M. Antonova *et al.*, “Baby MIND: a magnetized segmented neutrino detector for the WAGASCI experiment,” *Journal of Instrumentation*, vol. 12, p. C07028–C07028, 7 2017.
- [8] “Kuraray Wavelength Shifting Fibers.” <http://kuraraypsf.jp/psf/ws.html>.
- [9] M. Yokoyama *et al.*, “Application of Hamamatsu MPPCs to T2K neutrino detectors,” *Nuclear Instruments and Methods in Physics Research Section A: Accelerators, Spectrometers, Detectors and Associated Equipment*, vol. 610, no. 1, pp. 128–130, 2009. New Developments In Photodetection NDIP08.
- [10] D. G. Michael *et al.*, “The Magnetized steel and scintillator calorimeters of the MINOS experiment,” *Nuclear Instruments and Methods in Physics Research Section A: Accelerators, Spectrometers, Detectors and Associated Equipment*, vol. 596, pp. 190–228, 2008.
- [11] L. Aliaga *et al.*, “Design, Calibration, and Performance of the MINERvA Detector,” *Nuclear Instruments and Methods in Physics Research Section A: Accelerators, Spectrometers, Detectors and Associated Equipment*, vol. 743, pp. 130–159, 2014.
- [12] C. F. Barnaby and J. C. Barton, “Ageing of Plastic Scintillators,” *Journal of Scientific Instruments*, vol. 39, 4 1962.
- [13] V. Senchishin *et al.*, “New radiation stable and long-lived plastic scintillator for the SSC,” 11 1993. FNAL-TM-1866.

- [14] A. Artikov *et al.*, “Properties of the Ukraine polystyrene-based plastic scintillator UPS 923A,” *Nuclear Instruments and Methods in Physics Research Section A: Accelerators, Spectrometers, Detectors and Associated Equipment*, vol. 555, no. 1, pp. 125–131, 2005.
- [15] T. Zhou, H. He, and X. Sheng, “The long-term stability of plastic scintillator for electromagnetic particle detectors,” *Proceedings of the 32nd International Cosmic Ray Conference, ICRC 2011*, vol. 4, pp. 346–349, 1 2011.
- [16] M. Loyd *et al.*, “Accelerated aging test of new plastic scintillators,” *Nuclear Instruments and Methods in Physics Research. Section A, Accelerators, Spectrometers, Detectors and Associated Equipment*, vol. 949, 10 2019.
- [17] E. D. Sword, “Humidity-induced damage in polyvinyl toluene and polystyrene plastic scintillator,” in *2017 IEEE International Symposium on Technologies for Homeland Security (HST)*, pp. 1–4, 1 2017.
- [18] M. Loyd, *Investigation of Environmental Degradation of Plastic Scintillators*. PhD thesis, Univeristy of Tennessee, 2019.
- [19] N. Zaitseva *et al.*, “Plastic scintillators stable for operating in wide ranges of humidity and temperature variations,” *Nuclear Instruments and Methods in Physics Research Section A: Accelerators, Spectrometers, Detectors and Associated Equipment*, vol. 954, p. 161709, 2020. Symposium on Radiation Measurements and Applications XVII.
- [20] R. P. Kambour, “A review of crazing and fracture in thermoplastics,” *Journal of Polymer Science: Macromolecular Reviews*, vol. 7, no. 1, pp. 1–154, 1973.
- [21] R. J. Cameron *et al.*, “Fogging in Polyvinyl Toluene Scintillators,” *IEEE Transactions on Nuclear Science*, vol. 62, no. 1, pp. 368–371, 2015.
- [22] E. Yousif and R. Haddad, “Photodegradation and photostabilization of polymers, especially polystyrene: review,” *Springerplus*, vol. 2, p. 398, 2013.
- [23] J. Timmer, “The UA1 Detector,” in *3rd Moriond Workshop: Antiproton-Proton Physics*, 1983.
- [24] S. Assylbekov *et al.*, “The T2K ND280 off-axis pi-zero detector,” *Nuclear Instruments and Methods in Physics Research Section A: Accelerators, Spectrometers, Detectors and Associated Equipment*, vol. 686, pp. 48–63, 2012.
- [25] N. Abgrall *et al.*, “Time projection chambers for the T2K near detectors,” *Nuclear Instruments and Methods in Physics Research Section A: Accelerators, Spectrometers, Detectors and Associated Equipment*, vol. 637, no. 1, pp. 25–46, 2011.
- [26] P. A. Amaudruz *et al.*, “The T2K Fine-Grained Detectors,” *Nuclear Instruments and Methods in Physics Research Section A: Accelerators, Spectrometers, Detectors and Associated Equipment*, vol. 696, pp. 1–31, 2012.
- [27] D. Allan *et al.*, “The Electromagnetic Calorimeter for the T2K Near Detector ND280,” *Journal of Instrumentation*, vol. 8, p. P10019, 2013.
- [28] S. Aoki *et al.*, “The T2K Side Muon Range Detector (SMRD),” *Nuclear Instruments and Methods in Physics Research Section A: Accelerators, Spectrometers, Detectors and Associated Equipment*, vol. 698, pp. 135–146, 2013.
- [29] H. Pernegger and M. Friedl, “Convolutd Landau and Gaussian Fitting Function.” https://root.cern/doc/master/langaus_8C.html.
- [30] K. Abe *et al.*, “T2K ND280 Upgrade - Technical Design Report,” 1 2019. CERN-SPSC-2019-001 (SPSC-TDR-006).

- [31] K. Abe *et al.*, “Sensitivity of the T2K accelerator-based neutrino experiment with an Extended run to 20×10^{21} POT,” 7 2016. arXiv:1607.08004v1 [hep-ex].
- [32] K. Abe *et al.*, “Hyper-Kamiokande Design Report,” 5 2018. arXiv:1805.04163v2 [physics.ins-det].
- [33] G. DeZoort *et al.*, “Performance of Wavelength-Shifting Fibers for the Mu2e Cosmic Ray Veto Detector,” 11 2015. arXiv:1511.06225v1 [physics.ins-det].
- [34] E. C. Dukes *et al.*, “Performance of Wavelength-Shifting Fibers for the Mu2e Cosmic Ray Veto Detector,” *Journal of Instrumentation*, vol. 13, pp. P12028–P12028, 12 2018.
- [35] Hamamatsu Photonics K.K., “MPPC Technical Note.”
https://www.hamamatsu.com/resources/pdf/ssd/mppc_kapd9008e.pdf.
- [36] “Data release for ‘Scintillator ageing of the T2K near detectors from 2010 to 2021’.”
[10.5281/zenodo.6783269](https://zenodo.org/record/105281).