



King's Research Portal

DOI:

[10.1021/acs.macromol.7b01417](https://doi.org/10.1021/acs.macromol.7b01417)

Document Version

Peer reviewed version

[Link to publication record in King's Research Portal](#)

Citation for published version (APA):

López-Pérez, P. M., M. P. da Silva, R., Strehin, I., Kouwer, P. H. J., Leeuwenburgh, S. C. G., & Messersmith, P. B. (2017). Self-healing hydrogels formed by complexation between calcium ions and bisphosphonate-functionalized star-shaped polymers. *MACROMOLECULES*, *50*(21), 8698–8706.
<https://doi.org/10.1021/acs.macromol.7b01417>

Citing this paper

Please note that where the full-text provided on King's Research Portal is the Author Accepted Manuscript or Post-Print version this may differ from the final Published version. If citing, it is advised that you check and use the publisher's definitive version for pagination, volume/issue, and date of publication details. And where the final published version is provided on the Research Portal, if citing you are again advised to check the publisher's website for any subsequent corrections.

General rights

Copyright and moral rights for the publications made accessible in the Research Portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognize and abide by the legal requirements associated with these rights.

- Users may download and print one copy of any publication from the Research Portal for the purpose of private study or research.
- You may not further distribute the material or use it for any profit-making activity or commercial gain
- You may freely distribute the URL identifying the publication in the Research Portal

Take down policy

If you believe that this document breaches copyright please contact librarypure@kcl.ac.uk providing details, and we will remove access to the work immediately and investigate your claim.

This document is confidential and is proprietary to the American Chemical Society and its authors. Do not copy or disclose without written permission. If you have received this item in error, notify the sender and delete all copies.

Self-healing hydrogels formed by complexation between calcium ions and bisphosphonate-functionalized star-shaped polymers

Journal:	<i>Macromolecules</i>
Manuscript ID	ma-2017-014175.R1
Manuscript Type:	Article
Date Submitted by the Author:	30-Sep-2017
Complete List of Authors:	Lopez Perez, Paula; Radboudumc, Biomaterials da Silva, Ricardo; King's College London, Centre for Craniofacial & Regenerative Biology Strehin , Iossif ; Northwestern University, Kouwer, Paul; Radboud University Nijmegen, Institute for Molecules and Materials Leeuwenburgh, Sander; Radboudumc, Biomaterials Messersmith, Phillip; University of California, Berkeley, Departments of Bioengineering and Materials Science and Engineering

SCHOLARONE™
Manuscripts

1
2
3
4
5
6
7 Self-healing hydrogels formed by complexation
8
9
10
11 between calcium ions and bisphosphonate-
12
13
14
15 functionalized star-shaped polymers
16
17
18
19
20

21 *Paula M. Lopez-Perez*^{a, b, ‡}, *Ricardo M. P. da Silva*^{c, ‡, *}, *Iossif Strehin*^a, *Paul H. J. Kouwer*^d,
22
23 *Sander C. G. Leeuwenburgh*^b, *Phillip B. Messersmith*^{a, e, *}
24
25

26
27 ^a Biomedical Engineering Department, Materials Science and Engineering Department, Chemical
28 and Biological Engineering Department, Chemistry of Life Processes Institute, Institute for
29 Bionanotechnology in Medicine, Robert H. Lurie Comprehensive Cancer Center, Northwestern
30 University, Evanston, IL, USA
31
32
33
34
35

36
37 ^b Department of Biomaterials, Radboud University Medical Center, Nijmegen, The Netherlands
38
39

40
41 ^c Centre for Craniofacial and Regenerative Biology, King's College London, London, SE1 9RT,
42 UK
43
44
45

46
47 ^d Institute for Molecules and Materials, Radboud University, Nijmegen, The Netherlands.
48
49

50
51 ^e Departments of Bioengineering and Materials Science and Engineering, University of
52 California, Berkeley, CA, USA
53
54
55
56
57
58
59
60

ABSTRACT

Star-shaped poly(ethylene glycol) (PEG) chain termini were functionalized with alendronate to create transient networks with reversible crosslinks upon addition of calcium ions. The gelation ability of alendronate-functionalized PEG was greatly dependent on the number of arms and arm molecular weight. After mixing polymer and calcium solutions, the formed hydrogels could be cut and then brought back together without any visible interface. After 2 minutes of contact, their connection was strong enough to allow for stretching without tearing through the previous fracture surface. Oscillatory rheology showed that the hydrogels recovered between 70 and 100% of the original storage and loss modulus after rupture. Frequency sweep measurements revealed a liquid-like behavior at lower frequencies and solid-like at high frequencies. Shifting frequency curves obtained at different calcium and polymer concentrations, all data collapsed in a single common master curve. This time-concentration superposition reveals a common relaxation mechanism intrinsically connected to the calcium-bisphosphonate complexation equilibrium.

INTRODUCTION

Hydrogels are materials composed of hydrophilic polymer strands connected to each other at crosslinking points. The resulting three-dimensional network can be regarded as a huge macromolecule that spans the entire volume of the system. Due to the hydrophilic nature of the constituting polymeric chains, hydrogels can absorb considerable amounts of water. This feature makes them appropriate for a wide variety of technological applications, including biomaterials for drug delivery and tissue regeneration. Traditionally, hydrogels are created by irreversible bonds between the polymer chains that form permanent networks. An important feature of these materials is that their stiffness falls within the range of soft biological tissues.¹ Nevertheless, a permanent network cannot recover its initial integrity after rupture. For applications in regenerative medicine, non-degradable permanent networks do not allow cellular migration. To obviate this problem, hydrogels were designed with star shaped multi-arm PEG macromers crosslinked through peptide sequences susceptible to degradation by matrix metalloproteinases.^{2,3} However, cellular infiltration is achieved at the expense of the original network integrity. In biological tissues, nature solves this problem by continuously breaking down and reconstructing the extracellular matrix. The complexity and degree of sophistication of these natural materials is still far beyond the current state of the art of synthetic materials.

A simple approach that holds great potential to overcome this problem is the creation of transient networks, in which polymer strands are connected by reversible bonds. Several types of reversible chemical bonds of different strength have been used to design self-healing PEG hydrogels, such as reversible covalent bonds,^{4,5} hydrogen bonding^{6,7} and coordination bonds.⁸⁻¹² These transient hydrogels are structurally similar to a permanent network, but dynamically different since the network configuration is constantly being reshaped. In this way, transient

1
2
3 networks are self-healing, which mean that they possess the ability to recover the integrity and,
4 at least to some extent, the original properties after damage. Hydrogels formed by reversible
5 bonds are expected to respond to cell-induced stress by rapidly breaking and reforming
6 elastically active crosslinks. Such systems facilitate complex cellular functions, while retaining
7 the overall mechanical environment. For instance, cell spreading, proliferation, and osteogenic
8 differentiation of mesenchymal stem cells (MSCs) were all enhanced in hydrogels with faster
9 bond dynamics.^{13,14}

10
11 To fully harness the benefits of self-healing soft materials, it is essential to obtain quantitative
12 understanding of the macromolecular dynamics relationship to the stress relaxation behavior of
13 the network. However, this is often complicated by convoluted effects of complex
14 supramolecular organization, heterogeneous polymeric structures or other competing
15 interactions. To overcome these limitations, regular star-shaped poly(ethylene glycol) (PEG)
16 polymers end-capped with reactive moieties have been used to create transient networks with
17 well-defined architectures.^{6,9-12,15} The rheological behavior of the simple star-shape geometry is
18 well described by classical polymer physics theory,^{16,17} facilitating analysis of the dynamic
19 network connectivity in terms of crosslinking reaction kinetics and equilibrium. Recently, we
20 found that catechol-modified star-shaped PEGs can be crosslinked through metal-coordination
21 with Al³⁺, Fe³⁺ and V³⁺ ions, while the viscoelastic properties of these materials were mainly
22 determined by variations in the kinetics of metal-catechol coordination bonds.¹² Although several
23 examples of transient PEG networks based on metal coordination bonds have been described
24 previously, most metals described are too toxic for biomedical applications. In the current study,
25 we describe a material based on biologically compatible components created by modifying the
26 chain-ends of star-shaped PEGs with a bisphosphonate (alendronic acid). Bisphosphonate drugs
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

1
2
3 are currently used to treat osteoporosis, Paget's disease of bone, malignancies metastatic to bone,
4 multiple myeloma, and hypercalcemia of malignancy.¹⁸⁻²⁰ They inhibit bone resorption^{19,20},
5
6 interact strongly with calcium at the surface of bone hydroxyapatite, and form complexes with
7
8 calcium ions in aqueous solution.²⁰⁻²² Herein, the complexation equilibrium between
9
10 bisphosphonate end-groups and calcium ions provides the rationale for the design of transient
11
12 crosslinks. We modified the free-chain ends of star-shaped PEGs comprising different number of
13
14 arms and arm molecular weight to evaluate the effect of the macromolecular architecture on
15
16 hydrogel network formation, stress relaxation and self-healing properties. We also studied how
17
18 changes in the reaction equilibrium and kinetics, induced by changes in either calcium or
19
20 polymer concentration, influenced network dynamics.
21
22
23
24
25
26
27

28 **EXPERIMENTAL SECTION**

29
30
31 **Materials.** Star-shaped PEG-OH molecules (8-arm with a tripentaerythritol core and 10, 20 or
32
33 40 kDa; 4-arm with a pentaerythritol core and 10 kDa) were purchased from JenKem
34
35 Technology USA Inc. Alendronic acid (98%) was acquired from AK Scientific Inc. Phosphate
36
37 buffered saline (PBS) solutions were prepared containing 2.67 mM KCl and 137.9 mM NaCl
38
39 (pH=7.4). Regular PBS solution was prepared with a total buffer concentration of 10 mM, and it
40
41 is referred only as PBS throughout the manuscript. Strongly buffered PBS solution was prepared
42
43 with a phosphate buffer concentration of 100 mM, referred as PBS(100 mM) solution. 1-ethyl-3-
44
45 (3-dimethylaminopropyl)carbodiimide hydrochloride (EDC) was purchased from TCI America.
46
47 N-hydroxysuccinimide (NHS), pyridine and all divalent salts were purchased from Sigma.
48
49
50
51

52 **Synthesis of alendronate-terminated PEG.** Alendronate-terminated PEGs were synthesized
53
54 by a three-step procedure (Fig. SI-1). First, N-hydroxysuccinimide-terminated PEGs (PNHS)
55
56 were synthesized in two steps as previously described.²³ Briefly, PEG-OH was dissolved in
57
58
59
60

1
2
3 chloroform (1 g/ml) together with 5 equiv. of glutaric anhydride. Pyridine (5 equiv.) was added
4
5 dropwise, and the reaction was refluxed at 80°C under inert atmosphere for 24 h. The reaction
6
7 product was diluted in MeOH, precipitated at -20°C for 1 h and centrifuged at -5°C, followed by
8
9 discarding the supernatant and repeating the procedure two more times. A white powder was
10
11 obtained after diethyl ether precipitation and vacuum drying overnight (97% yield and ~100%
12
13 conversion of the arm ends). Subsequently, the obtained glutaric acid terminated PEG (PG) was
14
15 dissolved in DMSO (0.5 g/ml) and reacted with an excess of NHS (10 equiv.) and EDC (10
16
17 equiv.) for 30 min at room temperature. The NHS activated PEG (PNHS) was purified again by
18
19 consecutive precipitation in MeOH and diethyl ether. A white powder was obtained after vacuum
20
21 drying. PNHS with 97% conversion of its arms was obtained with 81% yield.
22
23
24
25
26

27 Finally, alendronic acid was reacted with PNHS to produce alendronate terminated PEG
28
29 (PAA). A small test reaction was previously performed in an NMR tube using PBS (100 mM)
30
31 solution in D₂O. We followed the reaction kinetics for 3 h by ¹H-NMR (Fig. SI-2) to determine
32
33 the optimum pH to minimize competing hydrolysis of NHS, therefore maximizing coupling of
34
35 AA. Finally, alendronic acid was dissolved at 80 mM in PBS (100 mM) solution and the pH was
36
37 readjusted to 7.4 by adding 1 N NaOH solution. PNHS (1 wt%) was dissolved in the alendronic
38
39 acid solution and reacted for 4h at room temperature. The solution was dialyzed for 36 h against
40
41 water, and freeze-dried. The degree of modification was determined by proton nuclear magnetic
42
43 resonance (¹H-NMR) and is described in Table 1.
44
45
46
47

48 **Preparation of self-healing hydrogels.** Each sample was prepared by mixing equal volumes
49
50 of a PAA solution in PBS with a CaCl₂ aqueous solution. The concentration of each of these
51
52 solutions was chosen to obtain gels with final concentrations of polymer from 10 to 20 wt%, and
53
54 final calcium concentrations from 25 to 500 mM (see Table 2). The various formulations were
55
56
57
58
59
60

1
2
3 named after the number of arms (X), polymer M_w (Y) and modification (AA stands for
4 alendronic acid), using the nomenclature P(X) Y -AA. The mixture was stirred vigorously with a
5 spatula to form homogenous moldable gels. Subsequently, gelation was monitored by visual
6 inspection.
7
8
9
10

11
12 **Oscillatory rheology.** The viscoelastic properties of the gels were tested by oscillatory
13 rheology using an AR2000 Advanced Rheometer (TA Instruments) with parallel plate geometry
14 (20 mm diameter) at a fixed gap size of 500 μm . In general, the rheological properties of the gels
15 were analyzed after being homogenized for 3 min and incubated overnight into sealed test tubes.
16 An independent measurement was performed with freshly prepared gels (~ 3 min) to analyze if a
17 large curing time was required for gel attaining equilibrium viscoelastic properties. Strain sweep
18 tests were performed to determine the linear viscoelastic region, which was found to be greater
19 than 100% for most conditions (Fig. SI-3).
20
21
22
23
24
25
26
27
28
29
30
31

32 Frequency sweeps were performed at a constant strain of 5% by varying the angular frequency
33 between 0.1 and 100 rad/s). Prior to each frequency sweep test, a time sweep was performed for
34 5 min at 10 rad/s frequency and 5% strain to guarantee gel equilibration. Storage modulus (G'),
35 loss modulus (G''), and damping factor (and $\tan \delta$) were determined for star-shaped PEG
36 polymers of different molecular weight (M_w) and number of arms (f). Polymer and calcium
37 concentrations were varied around the arbitrary reference values of 15 wt% and 100 mM,
38 respectively. All measurements were performed at least in triplicate at constant temperature
39 (20°C) and under controlled humidity.
40
41
42
43
44
45
46
47
48
49
50

51 **Self-healing behavior.** Macroscopic self-healing properties of polymer gels were evaluated
52 visually by observing gel recovery after cutting a gel into two pieces with a surgical knife and
53 followed by fusing the two pieces without the application of a continuous external pressure. Gels
54
55
56
57
58
59
60

1
2
3 were also stained with either orange or black dyes to facilitate visualization. After cutting these
4
5 differently colored gels into pieces, the procedure was repeated by fusing gel pieces of different
6
7 colors.
8
9

10 Rheological failure-recovery tests were performed by applying large amplitude strains to break
11
12 the gel integrity followed by monitoring gel recovery. Initial viscoelastic properties were
13
14 measured at 5% strain and 10 rad/s angular frequency. After 5 min, strain was ramped until
15
16 1000% in 3 min to assure gel network disruption. After loss of gel integrity, the initial testing
17
18 conditions were restored to follow the time-dependent recovery of gel integrity for 10 min.
19
20 Several failure-recovery cycles were applied consecutively and the recovery was quantified by
21
22 comparing the storage modulus and damping factor before and after each rupture. All
23
24 measurements were performed at least in triplicate at constant temperature (20°C) and under
25
26 controlled atmospheric moisture.
27
28
29
30
31

32 **RESULTS AND DISCUSSION**

33
34
35 **Synthesis of star-shaped PEG-alendronate.** The terminus of each chain of star-shaped PEG
36
37 polymers was functionalized with alendronic acid (AA) (see Fig. 1b and Fig. SI-1 for a detailed
38
39 reaction scheme). Since alendronic acid is insoluble in most common organic solvents but
40
41 soluble in water at neutral and basic pH, the synthesis was performed in aqueous solutions.
42
43 However, in water the hydrolysis of NHS competes with coupling of AA, and the rates of both
44
45 reactions increase with pH. In order to determine suitable reaction conditions, we followed the
46
47 reaction kinetics for 3 h by ¹H-NMR. When using PBS buffer in D₂O, the AA coupling reaction
48
49 was complete in about 2 h (about 85% for all tested polymers, Fig. SI-2, Table 1), whereas the
50
51 remaining PEG-NHS was fully hydrolyzed (about 15%). PEGs with different number of arms (*f*)
52
53 and molecular weights (*M_w*) were designated as P(X)Y-AA, where X is the value of *f*, Y is the
54
55
56
57
58
59
60

nominal M_w in kDa, and AA refers to the functionalization with alendronic acid (see Fig. 1a). The effect of arm length on gelation was investigated by comparing 8-arm PEGs of different molecular weight ($M_a = 1.25, 2.5,$ or 5 kDa), while the effect of the number of arms was studied by comparing star-shaped PEGs of similar arm length ($M_a = M_w / f = 2.5$ kDa) but different number of arms ($f = 4$ or 8) (Table 1).

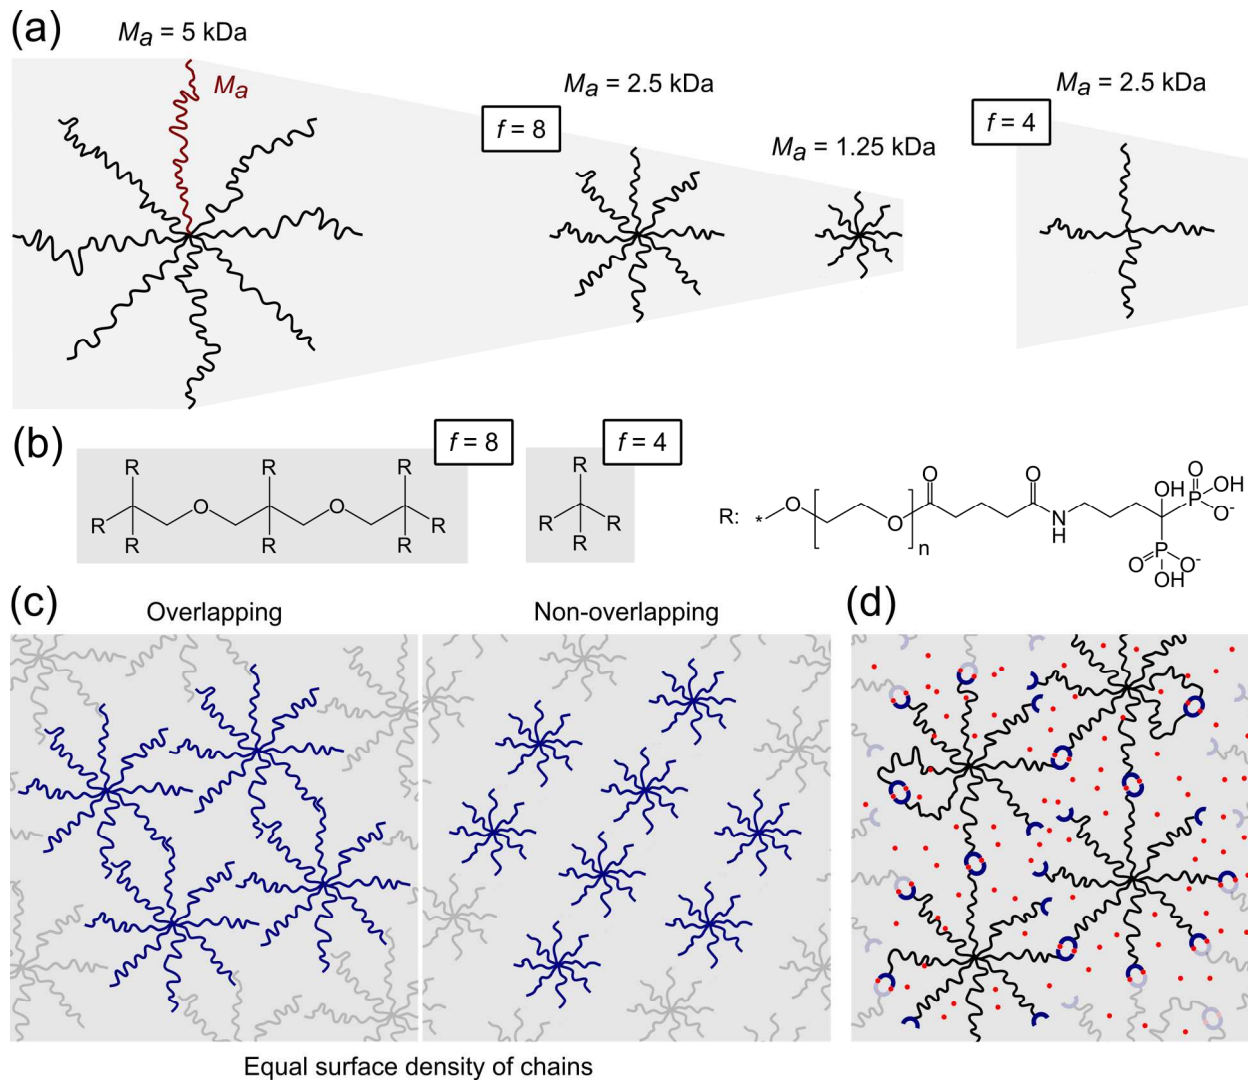


Figure 1. (a) PEG chains are represented by lines proportional in length to the molecular weight. (b) Chemical drawing of eight and four-arm PEG molecular cores and of an arm modified with alendronate. (c) Schematic representation of P(8)20-AA and P(8)10-AA solutions. The density of lines is constant, and depicts a polymer concentration where P(8)20-AA macromers overlap in

1
2
3 solution. At the same concentration, P(8)10-AA molecules cannot fill the entire space and do not
4
5 form a transient network. (d) Transient network showing free ends, intramolecular (loops) and
6
7 intermolecular (crosslinks) associations. Calcium ions and alendronate moieties are represented
8
9 by red dots and blue half-rings, respectively.
10
11

12
13 **Table 1.** Summary of multi-arm PEGs modified with alendronic acid at the chain termini:
14
15 molecular weight (M_w), number of arms (f), arm molecular weight (M_a), and overlapping
16
17 concentration (C^*).
18
19

Polymer	M_w (kDa)	f	M_a (kDa)	Yield ($^1\text{H-NMR}$)	$C^*=1/[\eta]$ (wt%)
P(8)10-AA	10	8	1.25	84%	12.3
P(8)20-AA	20	8	2.5	87%	7.5
P(8)40-AA	40	8	5	85%	4.6
P(4)10-AA	10	4	2.5	87%	7.4

20
21
22 Specific viscosity $[\eta]$ was calculated from Mark-Houwink-Sakurada parameters ($\alpha = 0.716$,
23
24 and K as function of f).²⁴
25
26

27
28 **Visual observation of gelation.** Star-shaped PEGs functionalized with AA were soluble in
29
30 water (and PBS) in the absence of Ca^{2+} . Mixing equal volumes of polymer and CaCl_2 solutions
31
32 at final polymer concentrations between 10 and 20 wt% and Ca^{2+} concentrations between 25 and
33
34 500 mM (Table 2) yielded either viscous solutions or solid-like self-standing materials, herein
35
36 referred as self-healing hydrogels. At the polymer concentration range used in this work, most
37
38 solutions are in the semidilute regime, with the exception of P(8)10-AA solutions at 10 wt% (see
39
40 Table 2). The overlapping concentration (C^*), which defines the transition between the dilute
41
42 and semidilute regimes, was calculated using the relation:¹⁷
43
44
45
46
47
48
49
50
51
52
53

$$C^* = \frac{1}{[\eta]}$$

1
2
3 where $[\eta]$ is the intrinsic viscosity. This can be calculated using the Mark-Houwink-Sakurada
4
5 equation:
6

$$[\eta] = K \cdot M_v^\alpha$$

7
8
9
10 We used the parameters determined by Comanita *et al.*²⁴ for star-shaped PEGs in water with
11
12 varying number of arms ($\alpha = 0.716$ as it would be expected for a good solvent, and K is a
13
14 function of f). The calculated C^* values are shown in the Table 1. Moreover, we can safely
15
16 assume that the transient networks were free of entanglements. The dependence of the molecular
17
18 weight between entanglements (M_e) on the volume fraction (φ) was described by Colby and
19
20 Rubinstein as:²⁵
21
22

$$M_e(\varphi) = M_e(\varphi = 1) \times \varphi^{-4/3}$$

23
24
25
26 The molecular weight between entanglements for the polymer melt ($\varphi = 1$, 100 %) is reported
27
28 to be 2.2 kDa.²⁶ As a result, at a polymer concentration between 10 and 20 wt% as used in our
29
30 experiments, an arm molecular weight of at least 20 kDa would be required to create one
31
32 entanglement. Therefore, besides the referred exception at the dilute regime (P(8)10-AA
33
34 solutions at 10 wt%), all other conditions are in the unentangled semidilute regime.
35
36
37

38
39 Gelation depended strongly on molecular weight (M_w), number of arms (f) and the Ca^{2+}
40
41 concentration. Eight-arm PEGs with a molecular weight 20 kDa (P(8)20-AA) displayed the most
42
43 pronounced gelation behavior. In fact, at 15 and 20 wt% polymer concentration, hydrogels were
44
45 formed for the entire range of tested Ca^{2+} concentrations, while a final polymer concentration of
46
47 10 wt% required a Ca^{2+} concentration higher than 100 mM for gelation. Hydrogels were not
48
49 obtained for most of the other AA functionalized PEGs except for P(8)10-AA, which only
50
51 formed hydrogels at high polymer (20 wt%) and Ca^{2+} concentrations (above 100 mM).
52
53
54
55 Generally, increasing both polymer and calcium concentrations formed stronger hydrogels.
56
57
58
59
60

Moreover, we found that either a lower number of arms ($f=4$) or a higher molecular weight ($M_w = 40$ kDa) hampered the formation of self-standing hydrogels.

Table 2. Visual screening of gelation at different polymer and CaCl₂ concentrations

Polymer	Concentration (wt%)	[AA] /mM	[Ca ²⁺] /mM				
			25	50	100	200	500
P(8)10-AA	10	80	✗	✗	✗	✗	✗
	15	120	✗	✗	✗	✗	✗
	20	160	□	□	✓	✓	✓
P(8)20-AA	10	40	✗	□	✓	✓	✓
	15	60	✓	✓	✓	✓	✓
	20	80	✓	✓	✓	✓	✓
P(8)40-AA	10	20	✗	✗	✗	✗	✗
	15	30	✗	✗	✗	✗	✗
	20	40	✗	✗	✗	✗	✗
P(4)10-AA	10	40	✗	✗	✗	✗	✗
	15	60	✗	✗	✗	✗	✗
	20	80	✗	✗	✗	✗	✗

Legend: (✗) viscous solution; (•) weak gels or very viscous solution; and (✓) gel formation. Grey table cells indicate dilute-regime. Polymers are in the semidilute regime for all other conditions.

Influence of number of arms (f) on gelation. We hypothesized that the ability of star-shaped PEG-alendronate macromers to form a transient network would increase with the number of functional groups per macromolecular precursor. A higher f corresponds to a greater probability of a macromolecule to participate simultaneously in multiple crosslinks. This is clearly manifested by comparing polymers with the same M_a , such as P(8)20-AA and P(4)10-AA), or

1
2
3 with the same M_w , such as P(8)10-AA and P(4)10-AA. In both cases, decreasing the number of
4 arms by a factor of 2 hampered the formation of an effective network (see Table 2). Therefore, a
5
6 threshold f value between 4 and 8 exists below which network formation is inhibited for the
7
8 conditions tested.
9
10

11
12 In reversibly crosslinked networks, the equilibrium concentration of intermolecular bonds
13 determines the effective number of crosslinks per macromolecular precursor (f'). If p_{inter} is the
14 probability of an arm forming an intermolecular bond, the number of effective crosslinks per
15 PEG precursor is given by $f' = p_{inter} \times f/2$. In our system, the formation of competing
16 intramolecular bonds with a certain probability p_{intra} cannot be ruled out. For strong
17 interactions, the equilibrium is pushed towards fully completion and the probability of free arms
18 is neglectable ($p_{free} \cong 0$). However, for weaker interactions $p_{free} \neq 0$ and:
19
20
21
22
23
24
25
26
27
28
29

$$p_{inter} + p_{intra} + p_{free} = 1$$

30
31 We assume that in the semidilute unentangled regime the interception of two different loops to
32 create mechanically interlocked chains is unlikely. Thus, the formation of intramolecular bonds
33 should mainly lead to elastically inactive loops in our experimental conditions (see Fig. 1d).
34 Therefore, only the intermolecular bonds are expected to create actual crosslinks.
35
36
37
38
39

40
41 As depicted in Table 2, P(8)20-AA and P(4)10-AA have the same molar concentration of AA
42 for all polymer concentrations, as well as similar overlapping concentration (Table 1). This
43 particular case allows for a more direct comparison of the underlying equilibrium, because
44 samples can be prepared with different number of arms but equal polymer, calcium and AA
45 concentrations, alongside the same concentration regime. While intramolecular bonds are
46 strongly favored in the dilute regime, at the vicinity of the overlapping concentration this effect
47 is progressively attenuated by the closer proximity of chains belonging to different molecules.
48
49
50
51
52
53
54
55
56
57
58
59
60

1
2
3 Therefore, an identical overlapping concentration means that the probability of forming an
4 intermolecular bond (p_{inter}) should be very similar in both cases, and the difference in number
5 of effective crosslinks per PEG molecule (f') derives primarily from the difference in the
6 number of arms (f). We found that hydrogels cannot be formed from P(4)10-AA, even at around
7 10 times excess of calcium. The random bond percolation model predicts that gelation does not
8 occur at conditions when $p_{inter}(f - 1) < 1$.^{17,27} As such, it is possible to estimate an upper limit
9 for the intermolecular bond frequency ($p_{inter} < 0.34$) for these two polymers. On the other
10 hand, P(8)20-AA polymer forms hydrogels and therefore $p_{inter}(f - 1) > 1$, which allows
11 calculation of a lower limit $p_{inter} > 0.14$ for the crosslinking frequency. This result shows that
12 the crosslinking reaction extension is relatively low, both for polymers with the best gelation
13 properties (P(8)20-AA) and for polymers that do not gel at all (P(4)10-AA). Therefore, the
14 stronger multivalency effect provided by a higher number of arms determines the gelation
15 behavior of star-shaped PEG crosslinked through alendronate-Ca²⁺ complexation. Moreover, it
16 also indicates that the existence of free arms and intramolecular bonds cannot be disregarded.
17 This conclusion can be generalized for all other conditions, which were tested for comparable
18 AA and calcium concentration ranges.

19
20
21 **Influence of arm length (M_a) on gelation.** At a constant number of arms and polymer
22 concentration, a larger arm length results in a decreased molar concentration of polymer ends,
23 resulting into a decreased p_{inter} . Accordingly, the effective number of crosslinks (f') is also
24 reduced. By comparing P(8)20-AA and P(8)40-AA at the same polymer concentration (see
25 Table 2), it can be observed that a two-fold increase in arm length, and consequently a two-fold
26 decrease in the molar concentration of AA, is enough to suppress gelation. The susceptibility of
27 gelation to AA concentration is consistent with the low intermolecular bond frequency described
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

1
2
3 in the previous section, even for hydrogel-forming polymer P(8)20-AA. Adding Ca^{2+} to
4
5 P(8)40-AA solutions still resulted in a noticeable increase in the solution viscosity, revealing that
6
7 polymer aggregates were formed, but the number of interchain associations was insufficient to
8
9 create a macroscopic hydrogel.
10
11

12
13 On the other hand, decreasing the arm length was also detrimental for the gelation capability of
14
15 the eight-arm PEG polymers. In fact, for P(8)10-AA macromolecules of shortest arm length, the
16
17 threshold polymer concentration for gelation (20 wt%) was two times higher than for P(8)20-AA
18
19 (10 wt%). Interestingly, the critical gelation concentration for both polymers (Table 2) was about
20
21 1.3 higher than the calculated overlapping concentration (Table 1). Below the overlapping
22
23 concentration the bond percolation theory cannot describe the network connectivity. Instead, the
24
25 number of intermolecular bonds (p_{inter}) required to form a continuous macromolecular network
26
27 increases with decreasing polymer concentration.²⁸ This means that P(8)10-AA did not form
28
29 hydrogels at lower polymer concentrations due to a direct effect of the macromolecular
30
31 configuration rather than an indirect effect related to the crosslinking extent (see Fig. 1c), which
32
33 in this case was expected to be higher since the concentration of AA is also higher.
34
35
36
37
38

39 The macromer with highest gelation capacity, P(8)20-AA, was tested in more detail using
40
41 oscillatory rheology in order to obtain insight in the viscoelastic properties and self-healing
42
43 ability of the formed hydrogels.
44
45

46 **Self-healing behavior.** Transparent, homogenous and moldable hydrogels were immediately
47
48 formed when P(8)20-AA and Ca^{2+} solutions were mixed. The hydrogels formed through the
49
50 interaction of star-shape PEG-AA with calcium ions possessed self-healing capability. As can be
51
52 seen in Fig. 2a, cylinders composed of 15 wt% polymer and 100 mM CaCl_2 stained with
53
54 different dyes were cut in two pieces, and then brought back together. No obvious border was
55
56
57
58
59
60

1
2
3 observed after fusing both parts of the gel, and after 2 min of contact their connection was strong
4
5 enough to allow for stretching without tearing through the previous fracture surface. This
6
7 phenomenon was repeatable and effective irrespective of the position of the cut or fusion.
8
9 Moreover, no liquid flow was detected through the interface at the bare eye, as colors did not
10
11 mix or fade within the experimental timescale (up to six hours). This revealed that the observed
12
13 macroscopic self-healing was a local interfacial phenomenon. Nonetheless, self-healing also
14
15 occurred at these materials bulk as shown in Fig. 2b, which depicts the quantification of self-
16
17 healing behavior of the same gels by oscillatory rheology. In this experiment, a strain from 5 to
18
19 1000% was applied to cause gel failure, as manifested by a sudden increase in the damping
20
21 factor, accompanied by a decrease in both storage and loss modulus. When strain was brought to
22
23 its initial value, a very fast recovery was observed for each of these three variables. Failure-
24
25 recovery cycles were repeated several times without a measurable loss of the self-healing
26
27 capability. In fact, the storage modulus recovery was 73 ± 2 , 77 ± 5 , and 96 ± 4 % after the first,
28
29 second and third failure cycle, respectively. This is comparable to other star-shaped PEG self-
30
31 healing hydrogels reported in the literature.^{10,15,29,30} Furthermore, the damping factor returned to
32
33 its original level almost instantaneously for every cycle. A similar self-healing capability was
34
35 observed for all P(8)20-AA gelation conditions tested irrespective of the polymer or Ca^{2+}
36
37 concentrations (see Fig. SI-4).
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60


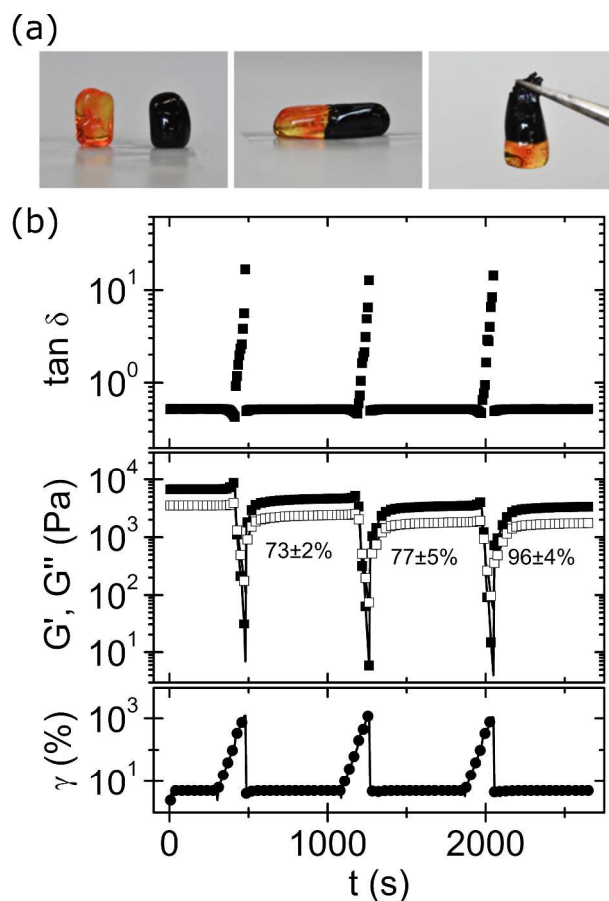


Figure 2. Self-healing behavior of the hydrogel formed from 15 w% P8(20)-AA and 100 mM CaCl_2 . (a) The gel was formed into a cylinder, cut in two pieces (left), fused together (center) and stretched without fracture (right). The pieces were stained with dyes of different color to improve visualization of the healing process. (b) Failure-recovery tests where gel failure was induced by an increase in strain from 5 to 1000%. The recovery of the storage modulus for each cycle is shown in the picture. Measurements were performed at 20°C and a constant angular frequency of 10 rad/s.

Effect of polymer concentration on viscoelastic properties. Frequency sweep experiments were performed both on freshly prepared hydrogels (~ 3 min) and after incubation overnight in a sealed test tube. The rheological properties were not affected by aging (Fig. SI-5), revealing that

1
2
3 crosslinking was a fast process reaching equilibrium in less than 3 minutes. Frequency sweep
4 experiments revealed solid-like properties ($G' > G''$) at high frequencies and viscous liquid-like
5 behavior ($G' < G''$) properties at lower frequencies for all samples (Fig. 3). As expected, an
6 increase in polymer concentration resulted into higher G' and G'' , and simultaneously lower
7 $\tan \delta$ values at the same frequency. The plateau modulus ($G_0 \sim 4 \times 10^4$ Pa for 15 wt%) was
8 comparable to other transient networks based on star-shaped PEG hydrogels as reported in the
9 literature.^{4,9,11}

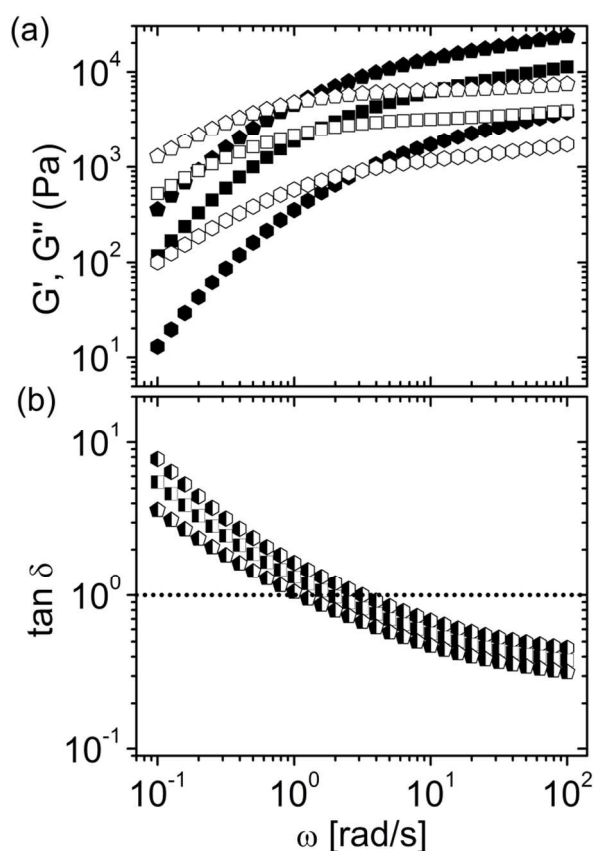

49
50
51
52
53
54
55
56
57
58
59
60

Figure 3. Frequency sweeps of P(8)20-AA ionic gels formed at polymer concentrations of 10 (hexagons), 15 (squares) and 20 wt% (pentagons) at a calcium concentration of 100 mM: (a) Storage (G') and loss (G'') moduli are represented with solid and open symbols, respectively; (b) Damping factor ($\tan \delta$). All measurements were performed at 20°C and 5% strain.

In Figure 3 a systematic shift of G' , G'' and $\tan \delta$ curves can be observed with increasing polymer concentration (C_p). We shifted the dynamic data of Figure 3 both horizontally (a_{C_p}) and vertically (b_{C_p}) to build a polymer concentration-invariant master curve, according to the following equations:

$$G'(\omega) = b_{C_p} \cdot G'_{ref}(a_{C_p} \cdot \omega)$$

$$G''(\omega) = b_{C_p} \cdot G''_{ref}(a_{C_p} \cdot \omega)$$

where G'_{ref} and G''_{ref} are the storage and loss modulus of the reference data, respectively. We used the method proposed by Honerkamp and Weese³¹ and a reference polymer concentration of 15 wt%. Running a global fitting ($R^2 = 0.998$, $\chi^2 = 0.714$), all data collapsed in a single master curve (Fig. 4a). The shift factors are plotted against polymer concentration in Figure 4b (symbols) and simple scaling laws were found (lines in Fig. 4b). The vertical shift factor accounts for variations in the plateau elastic modulus due to changes in polymer concentration ($G_0 \sim b_{C_p}$), whereas the horizontal shift factor reflects the dependence of the characteristic network relaxation time on polymer concentration ($\tau \sim a_{C_p}$), therefore:

$$\tau \sim a_{C_p} \sim C_p^\alpha$$

$$G_0 \sim b_{C_p} \sim C_p^\beta$$

with $\alpha = 1.5$ and $\beta = 2.3$. The zero-shear viscosity (η_0) dependence on polymer concentration is described by the power law:

$$\eta_0 = \tau \cdot G_0 \sim C_p^{(\alpha+\beta)} = C_p^{3.8}$$

Although there is a growing interest in self-healing hydrogels based on star-shaped polymers crosslinked through reversible interactions at the chains termini,^{5,9-12,15,30,32} a rheological model which describes the stress relaxation behavior of this well-defined architecture is not yet

1
2
3 available. The Maxwell model was tentatively used to fit our rheological data, but not used
4
5 further due to a large deviation from Maxwellian behavior. Poor fitting is also depicted in many
6
7 literature reports, where a strong mismatch between fitted single Maxwell element models and
8
9 data is often shown both at high and low frequencies.³²⁻³⁴
10
11

12
13 In semidilute solutions in a good solvent, the relationship between G_0 and C_p is described for
14
15 both reversibly and irreversibly crosslinked networks by:^{35,36}
16
17

$$18 \quad G_0 \sim C_p^{9/4}$$

19
20 At higher frequencies, transient networks behave similarly to permanent ones. Consequently,
21
22 the plateau elastic modulus has the same polymer concentration dependence for both cases. The
23
24 plateau modulus of our system follows this expected scaling behavior.
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

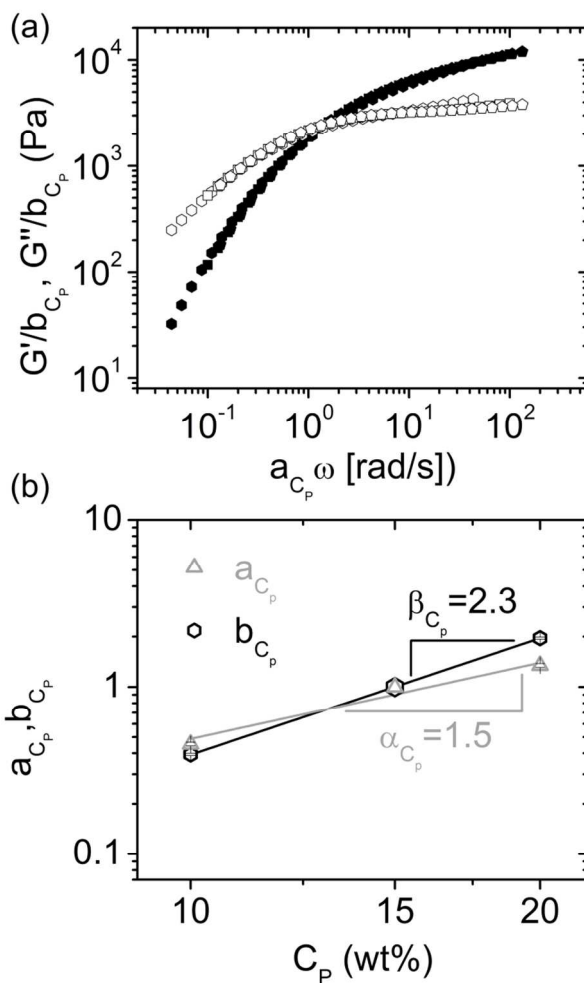


Figure 4. Superposition of frequency sweep data for polymer concentrations ranging from 10 to 20 wt% (as shown in Figure 3). (a) Polymer concentration invariant master curves of P(8)20-AA ionic gels formed at a calcium concentration of 100 mM. Storage (G') and loss (G'') moduli are represented by the same symbols as in Figure 2a. (b) Horizontal (a_{C_p}) and vertical (b_{C_p}) shifts were determined from the superposition fitting, and are shown as a function of polymer concentration.

On the other hand, there is not such a general relationship for τ and η_0 scaling behavior. Rubinstein and Semenov developed the so-called sticky Rouse³⁷ and sticky reptation³⁸ models to describe the chain dynamics of reversibly associating linear polymers with “sticky” points

1
2
3 distributed along the chain. For unentangled conditions in a good solvent, the sticky Rouse
4 model predicts 3 regimes with distinct concentration dependence of zero-shear viscosity
5
6 $(\eta_0 \sim C_p^{1.1-5.9})$.^{37,38} In turn, the sticky reptation model predicts 4 regimes for entangled
7
8 conditions in a good solvent $(\eta_0 \sim C_p^{3.75-8.5})$.³⁸ Both models assume strong association between
9
10 “sticky” points, and provide expressions for a renormalized bond lifetime that account for a
11
12 change in the relaxation time in conditions where there are almost no free chains in solution. In
13
14 such conditions, dissociated chains recombine several times before being able to find different
15
16 chain partners, which effectively increases the relaxation time of the network. There is a
17
18 remarkable similarity for the viscosity dependence on polymer concentration between our PEG
19
20 hydrogels and the predictions made by the sticky reptation model for entangled networks mostly
21
22 composed of intermolecular bonds $(\eta_0 \sim C_p^{3.75}, G_0 \sim C_p^{2.3}$ and $\tau \sim C_p^{1.45})$.³⁸ However, our
23
24 unentangled hydrogels do not fulfill the assumptions of the model and regime, besides the
25
26 existence of reversible crosslinks, precluding any analogy. For instance, an increased apparent
27
28 bond lifetime can be ruled out since our system is not strongly associated but coexists with
29
30 intramolecular bonds and free polymer ends. In these conditions, we expect the network
31
32 relaxation time to have a weak or non-dependence on bond formation rate $(1/\tau_{off})$, but to
33
34 depend mostly on bond lifetime (τ_{on}) . Craig and coworkers found that the characteristic
35
36 relaxation time of transient networks based on poly(4-vinylpyridine) is primarily governed by
37
38 bond dissociation rates and not equilibrium constants.^{34,39}

39
40
41 An alternative model developed by Cates³⁵ describes the dynamics of entangled linear
42
43 polymers in the presence of reversible chain-scission reactions, predicting $\eta_0 \sim C_p^{3.5}$ and
44
45 $\tau \sim C_p^{1.25}$ when breaking of flexible chains is much faster than reptation time $(\tau_{rep} \gg \tau_{on})$.
46
47 Although the model assumption of entangled linear chains is also not valid, the star-shaped
48
49
50
51
52
53
54
55
56
57
58
59
60

1
2
3 molecules can still be seen as chains entangled at the branching point with an extremely high
4 reptation time, such that bond breaking time dominates network stress relaxation. We found
5 similar, but slightly stronger dependencies for η_0 and τ .
6
7

8
9
10 Manakker et al³³ also found slightly stronger dependences ($\eta_0 \sim C_p^{4.2}$ and $\tau \sim C_p^{1.6}$) at similar
11 polymer concentration range for hydrogels based on inclusion complexes between a 8-arm star-
12 shaped PEG with chain ends modified with cholesterol and a telechelic linear PEG modified with
13 β -cyclodextrin. Rossow et al⁹ modified star-shaped PEG with terpyridine to create transient
14 networks based on coordination complexes. Network stress relaxation was tuned adding divalent
15 ions with different affinities (Co^{2+} and Zn^{2+}) and varying solvent polarity, which resulted in
16 various types of scaling behavior ($\eta_0 \sim C_p^{2.0-3.1}$ and $\tau \sim C_p^{0.4-1.2}$). Therefore, although the
17 polymer concentration dependencies found in this and other works³³ display similarity to Cate's
18 assumptions and predictions,³⁵ it seems that this behavior cannot be extrapolated to different
19 concentration regimes and/or association strengths. The development of theoretical models to
20 predict stress-relaxation of star-shaped transient networks will be highly valuable to the
21 understanding and engineering of this type of soft materials.
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38

39 **Effect of calcium concentration on viscoelastic properties.** The effect of calcium
40 concentration on the rheological properties of the transient networks was also studied at constant
41 polymer concentration (15 wt%). The G' and G'' curves resulting from frequency sweep
42 measurements presented shape similarity for the entire range of tested calcium concentrations.
43 These curves were shifted both horizontal and vertically by means of the procedure described
44 above, but with shift factors as a function of $[\text{Ca}^{2+}]$.
45
46
47
48
49
50
51
52

$$G'(\omega) = b_{[\text{Ca}^{2+}]} \cdot G'_{ref}(a_{[\text{Ca}^{2+}]} \cdot \omega)$$

$$G''(\omega) = b_{[\text{Ca}^{2+}]} \cdot G''_{ref}(a_{[\text{Ca}^{2+}]} \cdot \omega)$$

All calcium concentration dependent data fitted into a common master curve as depicted in Figure 5a, where the curve for a calcium concentration of 100 mM was used as reference. The calcium dependent shift factors are plotted in Figure 5b.

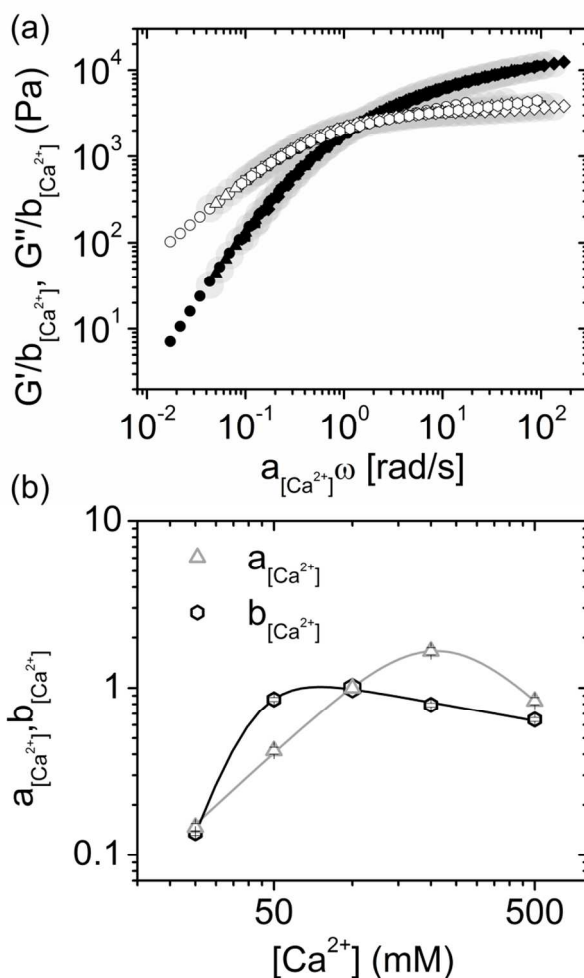


Figure 5. Superposition of frequency sweeps for calcium concentrations ranging from 25 to 500 mM. (a) Calcium concentration invariant master curves of P(8)20-AA ionic gels formed at a polymer concentration of 15 wt%. Polymer concentration invariant master curves from figure 3 and shown as grey large background symbols. (b) Horizontal ($a_{[Ca^{2+}]}$) and vertical ($b_{[Ca^{2+}]}$) shift factors were determined from the superposition fitting, and are shown as function of Calcium concentration.

1
2
3 The horizontal shift factor $a_{[Ca^{2+}]}$ accounts for changes in the relaxation time, and thus in
4 network connectivity dynamics. This means that the horizontal shift factor dependence on
5 calcium concentration derives primarily from the way this concentration affects both the
6 dissociation reaction rate ($1/\tau_{on}$) and the number of bonds ($f \times p_{inter}$) that should be disrupted to
7 allow the displacement of the star-shaped molecules. Figure 5b shows that the horizontal shift
8 factor increased up to a calcium concentration of 200 mM, indicating that the relaxation
9 spectrum was displaced to longer times (lower frequencies) with increasing calcium
10 concentration. In turn, above 200 mM the relaxation spectrum shifted back to shorter relaxation
11 times (higher frequencies), and consequently $a_{[Ca^{2+}]}$ decreased with increasing calcium
12 concentration. This behavior at high calcium concentration can be explained by the formation of
13 complexes with different stoichiometry and stability. It was reported that bisphosphonates can
14 form chelates of different stoichiometry with calcium.²¹ Moreover, at pH 7.2 alendronate forms
15 salts with different stoichiometry and solubility depending on the ratio between calcium and
16 alendronate. Interestingly the alendronate solubility decreases up to a ratio of 1.5, and increases
17 thereafter.⁴⁰ This indicates that complexes formed at higher calcium concentration are less stable,
18 which agrees with the observed shift of the stress relaxation spectrum to shorter times above a
19 calcium concentration threshold of around 200 mM.

20
21
22 A vertical shift factor $b_{[Ca^{2+}]}$ was also introduced to account for differences in the equilibrium
23 elastic modulus (G_0), which could originate from different concentrations of elastically effective
24 chains. In this case, variations of G_0 do not arise from variations of the polymer concentration
25 since this variable was kept constant for the entire dataset. In figure 5b it can be observed that
26 $b_{[Ca^{2+}]}$ increased sharply up to a calcium concentration of 50 mM, and remained approximately
27 constant at higher concentrations. The vertical shift accounts for variation in the equilibrium
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

1
2
3 elastic modulus, and represents an instantaneous snap-shot of the network, because at higher
4
5 frequencies bonds do not have time to dissociate and crosslinks behave as permanent
6
7 associations. Therefore, the vertical shift depends on the equilibrium density of crosslinks, but
8
9 should be insensitive to the individual rate constants of association and dissociation, provided
10
11 that the ratio between the two rate constants remain constant. The mismatch between the
12
13 dependence of both shift factors on the calcium concentration relies on their different physical
14
15 meanings (see Figure 5b). The stress relaxation depends on the collective disruption of network
16
17 bonds, which is independent on the instantaneous network connectivity that determines the
18
19 equilibrium elastic modulus.
20
21
22
23

24
25 In figure 5a, we also presented the polymer concentration invariant master curve (background
26
27 gray spots) for comparison with the calcium concentration master curve. The superposition
28
29 between both curves is remarkable, revealing that the relaxation mechanisms in the network all
30
31 scale similarly with both polymer and calcium concentrations. This is similar to what was
32
33 recently observed for catechol-modified star-shaped PEGs crosslinked through metal-
34
35 coordination (Al^{3+} , Fe^{3+} and V^{3+}).¹² In that study, the coordinating metal ion strongly influenced
36
37 the viscoelastic relaxation spectra, which were superimposed to form a coordination metal-
38
39 invariant master curve. Consequently, the differences in viscoelastic behavior were mainly
40
41 determined by variations in the dynamics of metal-catechol coordination bonds.¹¹ Our results are
42
43 in line with this previous study, which suggests that stress relaxation in self-healing hydrogels
44
45 based on star-shaped polymers is determined primarily by variations in bonding dynamics, and
46
47 that the underlying phenomena can be generalized. The development of specific models to
48
49 describe this class of materials will be crucial to understand and fully harness their applicability
50
51 as advanced materials.
52
53
54
55
56
57
58
59
60

CONCLUSIONS

Star-shaped poly(ethylene glycol) macromolecules with different geometric features (in terms of number of arms and arm molecular weight) were successfully end-functionalized with alendronate. The gelation behavior upon addition of calcium ions was highly dependent on this macromolecular architecture. Macromolecules containing four arms of 2.5 kDa each did not form hydrogels, indicating a low degree of chain association. On the other hand, polymers with same arm molecular weight but with twice as many arms formed self-healing hydrogels. However, gelation of eight arm polymers with shorter arms (1.25 kDa) was only observed for higher polymer concentrations (20 wt%), and gelation was completely hindered for higher arm molecular weight (5 kDa). Therefore, gelation occurred only in a small experimental window of number of arms and molecular weight. This peculiar behavior was explained by two opposite effects of increasing the arm molecular weight: first, it decreases the overlapping concentration, increasing likelihood of intermolecular bonds; second, it decreases the actual concentration of reactive chain ends, decreasing the likelihood of intermolecular bonds. For this reason, we have found an optimum intermediate arm molecular weight. When formed, the hydrogels could be cut and fused together within few minutes without any visible interface. Oscillatory rheology showed that the hydrogels recovered around 90% of the original storage and loss modulus after being ruptured by applying an extreme strain. Frequency sweeps revealed a liquid-like behavior at lower frequencies and solid-like behavior at high frequencies. The relaxation spectrum depended on both calcium and polymer concentrations. Storage and loss modulus curves could be shifted both horizontally and vertically to create a common master curve for both calcium and polymer concentrations. This time-concentration superposition revealed a common relaxation mechanism intrinsically connected to the complexation equilibrium, which suggested that stress

1
2
3 relaxation in our self-healing hydrogels based on alendronate-functionalized star-shaped PEGs is
4 governed primarily by variations in bonding dynamics. These insights contribute to a better
5 understanding of the self-healing behavior of PEG-based materials and may be a source of
6 inspiration for the design of advanced materials in application areas such as regenerative
7 medicine and bioprinting.
8
9
10
11
12
13
14
15

16 ASSOCIATED CONTENT

19 Supporting information.

20
21 Detailed scheme of reactions, kinetics of amidation and hydrolysis reactions, and additional
22 rheological data (PDF).
23
24
25
26
27

28 AUTHOR INFORMATION

31 Corresponding Author

32
33 *E-mail ricardo.silva@kcl.ac.uk (R.M.P.d.S.).
34
35
36

37
38 *E-mail philm@berkeley.edu (P.B.M.).
39
40

41 Author Contributions

42
43 ‡ PMLP and RMPdS contributed equally.
44
45

46 Note

47
48 The authors declare no competing financial interest.
49
50
51

52 ACKNOWLEDGEMENTS

1
2
3 P. M. L. P. and her research activities were funded by the Marie Curie FP7-PEOPLE-2011-IOF
4 program (ref. 299949). This research was partially supported by NIH grant (R37 DE014193) to
5
6
7
8 PBM.
9

10 11 REFERENCES

12
13
14 (1) Discher, D. E.; Mooney, D. J.; Zandstra, P. W. Growth Factors, Matrices, and Forces
15 Combine and Control Stem Cells. *Science* **2009**, *324* (5935), 1673–1677 DOI:
16
17 10.1126/science.1171643.
18
19

20
21
22 (2) Lutolf, M. P.; Hubbell, J. A. Synthetic Biomaterials as Instructive Extracellular
23 Microenvironments for Morphogenesis in Tissue Engineering. *Nat. Biotechnol.* **2005**, *23* (1), 47–
24
25 55 DOI: 10.1038/nbt1055.
26
27

28
29
30 (3) Leight, J. L.; Alge, D. L.; Maier, A. J.; Anseth, K. S. Direct Measurement of Matrix
31 Metalloproteinase Activity in 3D Cellular Microenvironments Using a Fluorogenic Peptide
32 Substrate. *Biomaterials* **2013**, *34* (30), 7344–7352 DOI: 10.1016/j.biomaterials.2013.06.023.
33
34
35

36
37
38 (4) McKinnon, D. D.; Domaille, D. W.; Cha, J. N.; Anseth, K. S. Biophysically Defined and
39 Cytocompatible Covalently Adaptable Networks as Viscoelastic 3D Cell Culture Systems. *Adv.*
40
41 *Mater.* **2014**, *26* (6), 865–872 DOI: 10.1002/adma.201303680.
42
43
44

45
46 (5) Rosales, A. M.; Anseth, K. S. The Design of Reversible Hydrogels to Capture
47 Extracellular Matrix Dynamics. *Nat. Rev. Mater.* **2016**, *1*, 15012 DOI:
48
49 10.1038/natrevmats.2015.12.
50
51

52
53
54 (6) Kieltyka, R. E.; Pape, A. C. H.; Albertazzi, L.; Nakano, Y.; Bastings, M. M. C.; Voets, I.
55
56 K.; Dankers, P. Y. W.; Meijer, E. W. Mesoscale Modulation of Supramolecular
57
58
59
60

1
2
3 Ureidopyrimidinone-Based Poly(ethylene Glycol) Transient Networks in Water. *J. Am. Chem.*
4
5 *Soc.* **2013**, *135* (30), 11159–11164 DOI: 10.1021/ja403745w.
6
7

8
9 (7) Guo, M.; Pitet, L. M.; Wyss, H. M.; Vos, M.; Dankers, P. Y. W.; Meijer, E. W. Tough
10
11 Stimuli-Responsive Supramolecular Hydrogels with Hydrogen-Bonding Network Junctions. *J.*
12
13 *Am. Chem. Soc.* **2014**, *136* (19), 6969–6977 DOI: 10.1021/ja500205v.
14
15

16
17 (8) Joo, J. H.; Ko, D. Y.; Moon, H. J.; Shinde, U. P.; Park, M. H.; Jeong, B. Ion and
18
19 Temperature Sensitive Polypeptide Block Copolymer. *Biomacromolecules* **2014**, *15* (10), 3664–
20
21 3670 DOI: 10.1021/bm500942p.
22
23

24
25 (9) Rossow, T.; Habicht, A.; Seiffert, S. Relaxation and Dynamics in Transient Polymer
26
27 Model Networks. *Macromolecules* **2014**, *47* (18), 6473–6482 DOI: 10.1021/ma5013144.
28
29

30
31 (10) He, L.; Fullenkamp, D. E.; Rivera, J. G.; Messersmith, P. B. pH Responsive Self-Healing
32
33 Hydrogels Formed by Boronate–catechol Complexation. *Chem. Commun.* **2011**, *47* (26), 7497–
34
35 7499 DOI: 10.1039/C1CC11928A.
36
37

38
39 (11) Fullenkamp, D. E.; He, L.; Barrett, D. G.; Burghardt, W. R.; Messersmith, P. B. Mussel-
40
41 Inspired Histidine-Based Transient Network Metal Coordination Hydrogels. *Macromolecules*
42
43 **2013**, *46* (3), 1167–1174 DOI: 10.1021/ma301791n.
44
45

46
47 (12) Holten-Andersen, N.; Jaishankar, A.; Harrington, M. J.; Fullenkamp, D. E.; DiMarco, G.;
48
49 He, L.; McKinley, G. H.; Messersmith, P. B.; Lee, K. Y. C. Metal-Coordination: Using One of
50
51 Nature's Tricks to Control Soft Material Mechanics. *J. Mater. Chem. B* **2014**, *2* (17), 2467–2472
52
53 DOI: 10.1039/C3TB21374A.
54
55
56
57
58
59
60

1
2
3 (13) Chaudhuri, O.; Gu, L.; Darnell, M.; Klumpers, D.; Bencherif, S. A.; Weaver, J. C.;
4 Huebsch, N.; Mooney, D. J. Substrate Stress Relaxation Regulates Cell Spreading. *Nat.*
5
6 *Commun.* **2015**, *6*, 6365 DOI: 10.1038/ncomms7365.
7
8

9
10
11 (14) Chaudhuri, O.; Gu, L.; Klumpers, D.; Darnell, M.; Bencherif, S. A.; Weaver, J. C.;
12 Huebsch, N.; Lee, H.; Lippens, E.; Duda, G. N.; Mooney, D. J. Hydrogels with Tunable Stress
13
14 Relaxation Regulate Stem Cell Fate and Activity. *Nat. Mater.* **2016**, *15* (3), 326–334 DOI:
15
16 10.1038/nmat4489.
17
18

19
20
21 (15) Sato, T.; Ebara, M.; Tanaka, S.; Asoh, T.-A.; Kikuchi, A.; Aoyagi, T. Rapid Self-
22
23 Healable Poly(ethylene Glycol) Hydrogels Formed by Selective Metal–phosphate Interactions.
24
25 *Phys. Chem. Chem. Phys.* **2013**, *15* (26), 10628–10635 DOI: 10.1039/C3CP50165E.
26
27

28
29 (16) Milner, S. T.; McLeish, T. C. B. Parameter-Free Theory for Stress Relaxation in Star
30
31 Polymer Melts. *Macromolecules* **1997**, *30* (7), 2159–2166 DOI: 10.1021/ma961559f.
32
33

34
35 (17) Rubinstein, M.; Colby, R. H. *Polymer Physics*, 1 edition.; Oxford University Press:
36
37 Oxford ; New York, 2003.
38
39

40
41 (18) Drake, M. T.; Clarke, B. L.; Khosla, S. Bisphosphonates: Mechanism of Action and Role
42
43 in Clinical Practice. *Mayo Clin. Proc.* **2008**, *83* (9), 1032–1045 DOI: 10.4065/83.9.1032.
44
45

46
47 (19) Rogers, M. J.; Crockett, J. C.; Coxon, F. P.; Mönkkönen, J. Biochemical and Molecular
48
49 Mechanisms of Action of Bisphosphonates. *Bone* **2011**, *49* (1), 34–41 DOI:
50
51 10.1016/j.bone.2010.11.008.
52
53

54
55 (20) Fleisch, H. Bisphosphonates: Mechanisms of Action. *Endocr. Rev.* **1998**, *19* (1), 80–100
56
57 DOI: 10.1210/edrv.19.1.0325.
58
59
60

1
2
3 (21) Szpak, M.; Matczak-Jon, E.; Kurzak, B. Potentiometric, ESI-MS and NMR Combined
4 Studies on the magnesium(II) and calcium(II) Complexation by Selected Bisphosphonic Acids in
5 Aqueous Solution. *Chem. Int.* **2014**, *68* (4), 321–328.
6
7

8
9
10
11 (22) Uchtman, V. A. Structural Investigations of Calcium Binding Molecules. II. Crystal and
12 Molecular Structures of Calcium Dihydrogen Ethane-1-Hydroxy-1,1-Diphosphonate Dihydrate,
13 $\text{CaC}(\text{CH}_3)(\text{OH})(\text{PO}_3\text{H})_2 \cdot 2\text{H}_2\text{O}$. Implications for Polynuclear Complex Formation. *J. Phys.*
14 *Chem.* **1972**, *76* (9), 1304–1310 DOI: 10.1021/j100653a014.
15
16
17

18
19
20
21 (23) Strehin, I.; Gourevitch, D.; Zhang, Y.; Heber-Katz, E.; Messersmith, P. B. Hydrogels
22 Formed by Oxo-Ester Mediated Native Chemical Ligation. *Biomater. Sci.* **2013**, *1* (6), 603–613
23 DOI: 10.1039/C3BM00201B.
24
25
26

27
28
29 (24) Comanita, B.; Noren, B.; Roovers, J. Star Poly(ethylene Oxide)s from Carbosilane
30 Dendrimers. *Macromolecules* **1999**, *32* (4), 1069–1072 DOI: 10.1021/ma981201e.
31
32
33

34
35 (25) Colby, R. H.; Rubinstein, M. Two-Parameter Scaling for Polymers in Θ Solvents.
36 *Macromolecules* **1990**, *23* (10), 2753–2757 DOI: 10.1021/ma00212a028.
37
38
39

40
41 (26) Niedzwiedz, K.; Wischnewski, A.; Pyckhout-Hintzen, W.; Allgaier, J.; Richter, D.;
42 Faraone, A. Chain Dynamics and Viscoelastic Properties of Poly(ethylene Oxide).
43 *Macromolecules* **2008**, *41* (13), 4866–4872 DOI: 10.1021/ma800446n.
44
45
46

47
48 (27) Ferry, J. D. *Viscoelastic Properties of Polymers, 3rd Edition*, 3 edition.; Wiley: New
49 York, 1980.
50
51
52
53
54
55
56
57
58
59
60

1
2
3 (28) Sakai, T.; Katashima, T.; Matsushita, T.; Chung, U. Sol-Gel Transition Behavior near
4 Critical Concentration and Connectivity. *Polym. J.* **2016**, *48* (5), 629–634 DOI:
5
6 10.1038/pj.2015.124.
7
8

9
10
11 (29) Li, Q.; Barrett, D. G.; Messersmith, P. B.; Holten-Andersen, N. Controlling Hydrogel
12 Mechanics via Bio-Inspired Polymer–Nanoparticle Bond Dynamics. *ACS Nano* **2016**, *10* (1),
13 1317–1324 DOI: 10.1021/acsnano.5b06692.
14
15
16

17
18
19 (30) Holten-Andersen, N.; Harrington, M. J.; Birkedal, H.; Lee, B. P.; Messersmith, P. B.;
20 Lee, K. Y. C.; Waite, J. H. pH-Induced Metal-Ligand Cross-Links Inspired by Mussel Yield
21 Self-Healing Polymer Networks with near-Covalent Elastic Moduli. *Proc. Natl. Acad. Sci.* **2011**,
22 *108* (7), 2651–2655 DOI: 10.1073/pnas.1015862108.
23
24
25
26

27
28
29 (31) Honerkamp, P. J.; Weese, J. A Note on Estimating Mastercurves. *Rheol. Acta* **1993**, *32*
30 (1), 57–64 DOI: 10.1007/BF00396677.
31
32
33

34
35 (32) Grindy, S. C.; Learsch, R.; Mozhdghi, D.; Cheng, J.; Barrett, D. G.; Guan, Z.;
36 Messersmith, P. B.; Holten-Andersen, N. Control of Hierarchical Polymer Mechanics with
37 Bioinspired Metal-Coordination Dynamics. *Nat. Mater.* **2015**, *advance online publication* DOI:
38 10.1038/nmat4401.
39
40
41
42

43
44
45 (33) van de Manakker, F.; Vermonden, T.; el Morabit, N.; van Nostrum, C. F.; Hennink, W.
46 E. Rheological Behavior of Self-Assembling PEG- β -Cyclodextrin/PEG-Cholesterol Hydrogels.
47 *Langmuir* **2008**, *24* (21), 12559–12567 DOI: 10.1021/la8023748.
48
49
50
51
52
53
54
55
56
57
58
59
60

1
2
3 (34) Yount, W. C.; Loveless, D. M.; Craig, S. L. Small-Molecule Dynamics and Mechanisms
4 Underlying the Macroscopic Mechanical Properties of Coordinatively Cross-Linked Polymer
5 Networks. *J. Am. Chem. Soc.* **2005**, *127* (41), 14488–14496 DOI: 10.1021/ja054298a.
6
7

8
9
10 (35) Cates, M. E. Reptation of Living Polymers: Dynamics of Entangled Polymers in the
11 Presence of Reversible Chain-Scission Reactions. *Macromolecules* **1987**, *20* (9), 2289–2296
12 DOI: 10.1021/ma00175a038.
13
14
15

16 (36) Khatory, A.; Lequeux, F.; Kern, F.; Candau, S. J. Linear and Nonlinear Viscoelasticity of
17 Semidilute Solutions of Wormlike Micelles at High Salt Content. *Langmuir* **1993**, *9* (6), 1456–
18 1464 DOI: 10.1021/la00030a005.
19
20
21
22
23
24

25 (37) Rubinstein, M.; Semenov, A. N. Thermoreversible Gelation in Solutions of Associating
26 Polymers. 2. Linear Dynamics. *Macromolecules* **1998**, *31* (4), 1386–1397 DOI:
27 10.1021/ma970617+.
28
29
30
31
32
33

34 (38) Rubinstein, M.; Semenov, A. N. Dynamics of Entangled Solutions of Associating
35 Polymers. *Macromolecules* **2001**, *34* (4), 1058–1068 DOI: 10.1021/ma0013049.
36
37
38
39

40 (39) Yount, W. C.; Loveless, D. M.; Craig, S. L. Strong Means Slow: Dynamic Contributions
41 to the Bulk Mechanical Properties of Supramolecular Networks. *Angew. Chem. Int. Ed.* **2005**, *44*
42 (18), 2746–2748 DOI: 10.1002/anie.200500026.
43
44
45
46
47


48 (40) Ostovic, D.; Brenner, G. S. Development of Subcutaneous and Intramuscular
49 Formulations of Calcium Alendronate Salts. *Drug Dev. Ind. Pharm.* **1995**, *21* (10), 1157–1169
50 DOI: 10.3109/03639049509026665.
51
52
53
54
55
56
57
58
59
60

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

1
2
3
4 For Table of Contents use only:
5
6
7
8
9
10

11
12 Self-healing hydrogels formed by complexation
13
14 between calcium ions and bisphosphonate-
15
16 functionalized star-shaped polymers
17
18
19
20
21
22
23
24
25

26 *Paula M. Lopez-Perez*^{a, b, ‡}, *Ricardo M. P. da Silva*^{c, ‡, *}, *Iossif Strehin*^a, *Paul H. Kouwer*^d,
27
28 *Sander C. G. Leeuwenburgh*^b, *Phillip B. Messersmith*^{a, e, *}
29
30
31
32
33

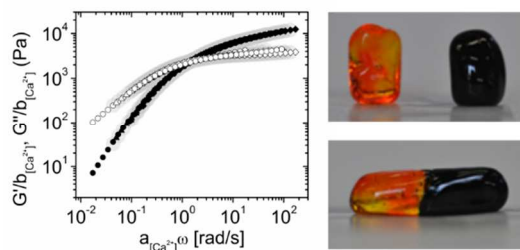

45
46 **KEYWORDS**
47

48 Self-healing, hydrogel, PEG, bisphosphonate, alendronate, calcium, dynamic biomaterials, stress
49
50 relaxation, ionomer, bone, star-shaped polymer
51
52
53
54
55
56
57
58
59
60